

---

This is an electronic reprint of the original article.  
This reprint may differ from the original in pagination and typographic detail.

Zelený, M.; Sozinov, A.; Björkman, T.; Straka, L.; Nieminen, R. M.  
**Ab initio study of properties of Co- and Cu- Doped Ni-Mn-Ga alloys**

*Published in:*  
International Conference on Martensitic Transformations, ICOMAT-2014

*DOI:*  
[10.1016/j.matpr.2015.07.356](https://doi.org/10.1016/j.matpr.2015.07.356)

Published: 01/01/2015

*Document Version*  
Publisher's PDF, also known as Version of record

*Published under the following license:*  
CC BY-NC-ND

*Please cite the original version:*  
Zelený, M., Sozinov, A., Björkman, T., Straka, L., & Nieminen, R. M. (2015). Ab initio study of properties of Co- and Cu- Doped Ni-Mn-Ga alloys. In *International Conference on Martensitic Transformations, ICOMAT-2014* (pp. S601-S604). (Materials Today: Proceedings; Vol. 2, No. Supplement 3). Elsevier.  
<https://doi.org/10.1016/j.matpr.2015.07.356>

---

This material is protected by copyright and other intellectual property rights, and duplication or sale of all or part of any of the repository collections is not permitted, except that material may be duplicated by you for your research use or educational purposes in electronic or print form. You must obtain permission for any other use. Electronic or print copies may not be offered, whether for sale or otherwise to anyone who is not an authorised user.

International Conference on Martensitic Transformations, ICOMAT-2014

## *Ab initio* study of properties of Co- and Cu- doped Ni-Mn-Ga alloys

M. Zelený<sup>a,b,\*</sup>, A. Sozinov<sup>c</sup>, T. Björkman<sup>d</sup>, L. Straka<sup>e</sup>, R. M. Nieminen<sup>d</sup>

<sup>a</sup>Institute of Materials Science and Engineering, NETME Centre, Faculty of Mechanical Engineering, Brno University of Technology, Technická 2896/2, CZ-61669 Brno, Czech Republic

<sup>b</sup>Central European Institute of Technology, CEITEC MU, Masaryk University, Kamenice 753/5, CZ-625 00 Brno, Czech Republic

<sup>c</sup>Material Physics Laboratory, Lappeenranta University of Technology, Laitaatsillantie 3, FI-57170 Savonlinna, Finland

<sup>d</sup>COMP/Department of Applied Physics, Aalto University School of Science, P.O. Box 11100, FI-00076 Aalto, Finland

<sup>e</sup>Aalto University School of Engineering, Laboratory of Engineering Materials, PL 14200, FI-00076 Aalto, Finland

---

### Abstract

The influence of Co and Cu doping on Ni-Mn-Ga alloy is investigated using the first-principles exact muffin-tin orbital method in combination with the coherent-potential approximation. The energy difference between the austenite (A) and the nonmodulated (NM) martensite  $\Delta E_{A-NM}$  depends linearly on the Cu concentration and distribution, with a minimum for all Cu at Mn sites and a maximum for all Cu at Ga sites. For alloys simultaneously doped by Co in Ni sublattice and Cu in Mn or Ga sublattice, the effects of the individual dopants on  $\Delta E_{A-NM}$  and  $(c/a)_{NM}$  are almost independent. The alloy with composition  $Ni_{46}Co_4Mn_{24}Ga_{22}Cu_4$  exhibits decreased equilibrium  $(c/a)_{NM}$  and increased  $\Delta E_{A-NM}$  in comparison with  $Ni_{50}Mn_{25}Ga_{25}$ , which is in agreement with the previous experimental results.

© 2015 The Authors. Published by Elsevier Ltd. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Selection and Peer-review under responsibility of the chairs of the International Conference on Martensitic Transformations 2014.

**Keywords:** Magnetic shape memory alloys; martensitic phase transitions; tetragonal deformation; *ab initio* calculations;

---

### 1. Introduction

The  $Ni_2MnGa$  Heusler alloy has attracted a lot of interest because it exhibits interesting magnetomechanical effects such as a giant magnetic-field-induced strain (MFIS). This phenomenon is a consequence of the coupling

---

\* Corresponding author. Tel.: +420-541-143-193; fax: +420-541-143-193.

E-mail address: [zeleny@fme.vutbr.cz](mailto:zeleny@fme.vutbr.cz)

between the magnetic microstructure and martensite twin microstructure combined with the high mobility of twin boundaries [1]. The MFIS occurs in martensite, i.e. below martensitic transformation, which takes place at  $T_M = 202$  K for stoichiometric  $\text{Ni}_2\text{MnGa}$ , whereas austenite with cubic ordered  $L2_1$  structure is stable above  $T_M$ . The Curie temperature  $T_C$  is about 376 K [2]. Controlling  $T_M$  and  $T_C$  is important task for the practical exploitation of the interesting properties of material. It can be achieved, for example, by using off-stoichiometric composition or doping with an additional element [3].

Several kinds of martensites have been observed in the Ni-Mn-Ga system. The modulated phases with ratio  $c/a < 1$  exhibit MFIS up to 10% [4]. Giant MFIS has never been reported for the nonmodulated (NM) martensite with a purely tetragonal lattice and  $(c/a)_{\text{NM}} \approx 1.17 - 1.23$  [5]. However, a MFIS of 12% has recently been reported in the NM phase for a structure with reduced  $(c/a)_{\text{NM}} = 1.147$ , achieved by simultaneous doping by 4 at. % of Cu and Co with the resulting alloy composition  $\text{Ni}_{46}\text{Co}_4\text{Mn}_{24}\text{Ga}_{22}\text{Cu}_4$  [6]. Doping also increased transformation temperatures of this alloy above room temperature,  $T_M = 330$  K and  $T_C = 393$  K.

Previous experimental investigations of Ni-Mn-Ga doping showed that  $T_M$  increases for the Co- and Cu-doped alloys deficient in Mn or Ga [7,8], whereas it decreases if Co or Cu replaces Ni atoms [3,9]. With the help of *ab initio* simulations the site preference has been clarified: Co exhibits tendency to occupy the Ni sublattice and Cu atoms always occupy the sublattice of the host elements in deficiency [10]. The energy difference between the austenite and the nonmodulated martensite  $\Delta E_{\text{A-NM}}$  has been also obtained from *ab initio* calculations. It correlates well with the experimentally determined  $T_M$ : a larger difference in total energies corresponds to a higher  $T_M$  [11].

In our previous theoretical work, we analyzed the development of calculated total energies along the tetragonal deformation path to obtain the equilibrium  $(c/a)_{\text{NM}}$  and  $\Delta E_{\text{A-NM}}$  [11]. The Cu doping in Ga sublattice results in a strong increase of  $\Delta E_{\text{A-NM}}$ , but just a small change of equilibrium  $(c/a)_{\text{NM}}$ . On the other hand, if Cu goes to Mn sublattice, the increase of  $\Delta E_{\text{A-NM}}$  is much smaller but a noticeable decrease of  $(c/a)_{\text{NM}}$  is seen. Both quantities  $\Delta E_{\text{A-NM}}$  and  $(c/a)_{\text{NM}}$  strongly decrease with increasing concentration of Co at Ni sites. Further, we have found that doping effects can be well estimated using a linear superposition of the effects of individual dopants for alloys doped simultaneously by Co in Ni site and Cu in Ga site (general formula  $\text{Ni}_{50-x}\text{Co}_x\text{Mn}_{25}\text{Ga}_{25-z}\text{Cu}_z$ ).

In this article, we extend the previous investigation of the simultaneous Co and Cu doping in Ni-Mn-Ga alloys. We especially focus on the Cu doping in Mn sublattice and we also show that the Cu distribution between Ga and Mn sublattices can be used for further fine tuning of properties. In the end we calculate and discuss the properties of alloy  $\text{Ni}_{46}\text{Co}_4\text{Mn}_{24}\text{Ga}_{22}\text{Cu}_4$ , which showed the most interesting behavior in the previous experiments [6].

## 2. Computational method

The first-principles calculations were carried out using the exact muffin-tin orbital (EMTO) method in combination with the full charge density (FCD) technique [13], which is suitable to accurately describe the total energy with respect to anisotropic lattice distortions such as tetragonal deformation. The chemical disorder caused by doping elements was included by using the coherent-potential approximation (CPA) [14,15]. The exchange correlation was described using the Perdew-Burke-Ernzerhof (PBE) generalized gradient approximation [16]. We used the same setting for calculations as in our previous work [11].

For alloys with different Cu and Co doping concentrations described by general formula  $\text{Ni}_{50-x}\text{Co}_x\text{Mn}_{25-y}\text{Ga}_{25-z}\text{Cu}_{y+z}$ , we calculated a series of total energies as a function of  $c/a$  in the range between  $c/a = 0.9$  and 1.4 at a constant volume, which describes the tetragonal deformation of austenite phase with  $L2_1$  structure ( $c/a = 1$ ). Calculated total energies are related to the energy of cubic structure for the given composition.

## 3. Results

For alloys with general formula  $\text{Ni}_{50-x}\text{Co}_x\text{Mn}_{25-y}\text{Ga}_{25}\text{Cu}_y$  where Cu atoms replace Mn atoms, we have found that the effects of Cu and Co additions are almost independent from each other, i.e. that the effects of combined doping can be estimated as the linear superposition of the effects of single element dopings. This is similar to the previously studied case of simultaneous doping with Cu replacing Ga atoms [12]. Figure 1(a) shows the total energy as a function of tetragonal ratio  $c/a$  for the alloy with constant concentration 5% of Co in Ni sublattice and different concentration  $z$  of Cu in Mn sublattice. The decrease of  $\Delta E_{\text{A-NM}}$ , which arises from doping by 5% of Co, is partially

compensated by Cu doping. However, even 7.5% Cu is not sufficient to compensate  $\Delta E_{A-NM}$  up to the value obtained for stoichiometric  $Ni_2MnGa$  alloy, because the effect of Cu doping in Mn sites is weaker than in the case when Cu is in Ga sites (see Fig 2(a) in Ref [12]). On the other hand, the equilibrium  $(c/a)_{NM}$  slightly decreases with increasing Cu concentration in Mn sites. Also alloys with constant 5% Cu concentration exhibit the same linear superposition of doping effects (Fig. 1(b)). Here, the  $(c/a)_{NM}$  is slightly decreased and  $\Delta E_{A-NM}$  is increased due to the presence of Cu in Mn site, however further increasing Co concentration in Ni sublattice decreases both quantities.

The effect of Cu distribution between Ga and Mn sublattices can be used for finer tuning of  $(c/a)_{NM}$  and  $\Delta E_{A-NM}$ . In alloys without any Co both quantities linearly increase with increasing Cu concentration in Ga sites and decreasing Cu concentration in Mn sites (Fig. 2(a)). The influence of Cu on  $\Delta E_{A-NM}$  is relatively strong, because there is a large difference between  $\Delta E_{A-NM}$  for  $Ni_{50}Mn_{20}Ga_{25}Cu_5$  and  $Ni_{50}Mn_{25}Ga_{20}Cu_5$  alloys (0.405 mRy/atom, 1 Ry = 13.606 eV =  $2.170 \cdot 10^{-18}$  J). Similar linear increasing of  $\Delta E_{A-NM}$  can be seen also for alloys with Co present in Ni sublattice (Fig. 2(b)). However, this effect is much weaker than in the case of no Co doping, because 5% of Co in Ni site causes that  $\Delta E_{A-NM}$  for both types of Cu doping will be closer to each other. The difference between  $\Delta E_{A-NM}$  for  $Ni_{45}Co_5Mn_{20}Ga_{25}Cu_5$  and  $Ni_{45}Co_5Mn_{25}Ga_{20}Cu_5$  alloys is 0.162 mRy/atom only. The influence of Cu distribution on  $(c/a)_{NM}$  is smaller than on  $\Delta E_{A-NM}$ , but still distinguishable. However, it also further decreases with increasing Co concentration. The difference between  $(c/a)_{NM}$  for alloys with no Co doping is 0.038, whereas if 5% of Co is present in Ni sublattice, these difference is 0.017 only.

To compare our results with experiment we calculated also total energies along the tetragonal deformation path for experimentally prepared alloy with composition  $Ni_{46}Co_4Mn_{24}Ga_{22}Cu_4$ . Experimental measurements shows reduction of  $(c/a)_{NM}$  and increased transformation temperature  $T_M$ . The latter should correspond to larger energy difference  $\Delta E_{A-NM}$ . As can be seen from Fig. 3 our results corresponds qualitatively to experimental findings:  $(c/a)_{NM}$  exhibit the same  $\approx 4\%$  decrease as in experiment (from 1.256 for stoichiometric  $Ni_2MnGa$  to  $(c/a)_{NM} = 1.208$ , compare with vertical lines in Fig. 3) and  $\Delta E_{A-NM}$  is increased from 0.379 mRy/atom to 0.420 mRy/atom.

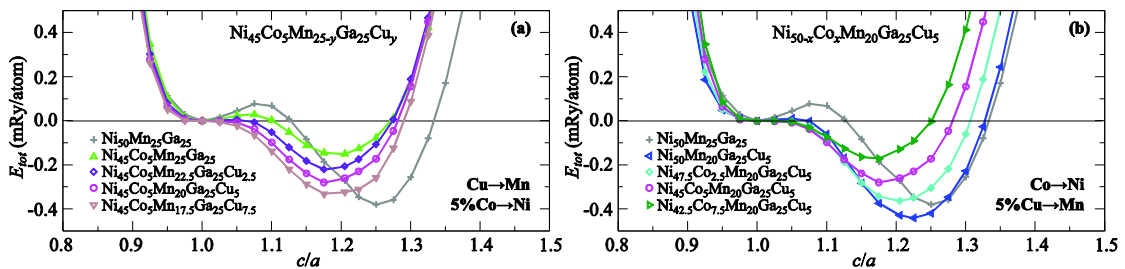


Fig. 1. Total energy as a function of the tetragonal ratio  $c/a$  for doped alloys with different concentrations  $y$  of Cu in the Mn sublattice and constant concentration 5% of Co in the Ni sublattice (a), and different concentration  $x$  of Co in the Ni sublattice and constant concentration 5% of Cu in the Mn sublattice (b).

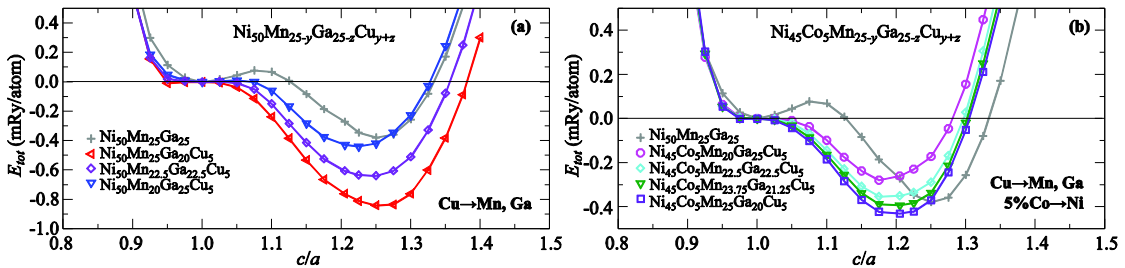


Fig. 2. Total energy as a function of the tetragonal ratio  $c/a$  for alloys with different distributions of Cu in the Mn and Ga sublattice with no Co doping (a), and with 5% of Co in the Ni sublattice (b).

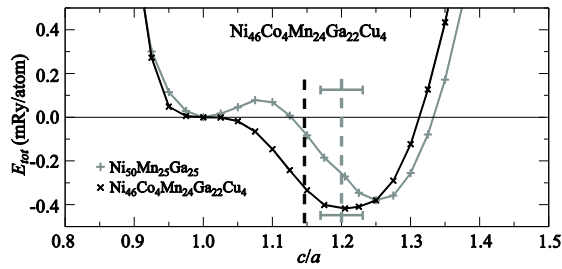


Fig. 3. Calculated total energy as a function of the tetragonal ratio  $c/a$  for experimentally prepared alloy with composition  $\text{Ni}_{46}\text{Co}_4\text{Mn}_{24}\text{Ga}_{22}\text{Cu}_4$ . Total energy of  $\text{Ni}_{50}\text{Mn}_{25}\text{Ga}_{25}$  alloy is also shown for comparison. Vertical dashed lines correspond to experimental values of  $c/a$ . For  $\text{Ni}_{50}\text{Mn}_{25}\text{Ga}_{25}$  alloy the horizontal error bar indicates the range of experimental  $c/a$  values [5].

#### 4. Conclusions

The Co and Cu doping of Ni-Mn-Ga Heusler alloys has been studied using the EMTO-CPA first-principles method. We have found the same independent effects of the individual dopants on  $\Delta E_{A-NM}$  and  $(c/a)_{NM}$  for alloys simultaneously doped by Co in Ni sublattice and Cu in Mn sublattice, which was already observed for the case where Cu was used instead of Ga. For alloys where Cu is distributed between Mn and Ga sublattices the  $\Delta E_{A-NM}$  increases linearly with increasing Cu concentration in Ga site and decreasing concentration in Mn site. The effect of Cu distribution on  $(c/a)_{NM}$  is small but clearly distinguishable. Our theoretical results are in a good agreement with experimental findings for alloy with composition  $\text{Ni}_{46}\text{Co}_4\text{Mn}_{24}\text{Ga}_{22}\text{Cu}_4$ .

#### Acknowledgements

This research has been supported by the Ministry of Education, Youth and Sports within the support programme „National Sustainability Programme I“ (Project NETME CENTRE PLUS – LO1202), by the Grant Agency of the Czech Republic (Project No. 14-22490S), and by the Academy of Finland through the Center of Excellence Program (2012–2017) and postdoctoral researcher Grant No. 134002. The access to the CERIT-SC computing and storage facilities provided under the programme Center CERIT Scientific Cloud, part of the Operational Program Research and Development for Innovations, Reg. No. CZ. 1.05/3.2.00/08.0144.

#### References

- [1] M.E. Gruner, P. Entel, I. Opahle, M. Richter, J. Mater. Sci. 43 (2008) 3825–3831.
- [2] P.J. Webster, K.R.A. Ziebeck, S. L. Town, M. S. Peak, Philos. Mag. B 49 (1984) 295–310.
- [3] D.E. Soto-Parra, X. Moya, L. Manosa, A. Planes, H. Flores-Zuniga, F. Alvarado-Hernandez, R.A. Ochoa-Gamboa, J.A. Matutes-Aquino, D. Rios-Jara, Philos. Mag. 90 (2010) 2771–2792.
- [4] A. Sozinov, A.A. Likhachev, N. Lanska, K. Ullakko, Appl. Phys. Lett. 80 (2002) 1746–1748.
- [5] N. Lanska, O. Söderberg, A. Sozinov, Y. Ge, K. Ullakko, V.K. Lindroos, J. Appl. Phys. 95, (2004) 8074.
- [6] A. Sozinov, N. Lanska, A. Soroka, W. Zou, Appl. Phys. Lett. 102 (2013) 021902.
- [7] C. Jiang, J. Wang, P. Li, A. Jia, H. Xu, Appl. Phys. Lett. 95 (2009) 012501.
- [8] J. Wang, C. Jiang, Scr. Mater. 62 (2010) 298–300.
- [9] V.G. Pushin, N.I. Kourov, A.V. Korolev, V.V. Marchenkov, E.B. Marchenkova, V.A. Kazantsev, N.N. Kuranova, A.G. Popov, Phys. Solid State 55 (2013) 2413–2421.
- [10] C.-M. Li, H.-B. Luo, Q.-M. Hu, R. Yang, B. Johansson, L. Vitos, Phys. Rev. B 84 (2011) 024206.
- [11] J. Chen, Y. Li, J.X. Shang, H.B. Xu, Appl. Phys. Lett. 89 (2006) 231921.
- [12] M. Zelený, A. Sozinov, L. Straka, T. Björkman, R.M. Nieminen, Phys. Rev. B 89 (2014) 184103.
- [13] L. Vitos, Computational Quantum Mechanics for Materials Engineers, Springer, London, 2007.
- [14] P. Soven, Phys. Rev. 156 (1967) 809–813.
- [15] L. Vitos, I.A. Abrikosov, B. Johansson, Phys. Rev. Lett. 87 (2001) 156401.
- [16] J.P. Perdew, K. Burke, M. Ernzerhof, Phys. Rev. Lett. 77 (1996) 3865–3868.