
This is an electronic reprint of the original article.
This reprint may differ from the original in pagination and typographic detail.

Gómez Millán, Gerardo; El Assal, Zouhair; Nieminen, Kaarlo; Hellsten, Sanna; Llorca, Jordi; Sixta, Herbert

Fast furfural formation from xylose using solid acid catalysts assisted by a microwave reactor

Published in:
Fuel Processing Technology

DOI:
[10.1016/j.fuproc.2018.10.013](https://doi.org/10.1016/j.fuproc.2018.10.013)

Published: 15/12/2018

Document Version
Peer-reviewed accepted author manuscript, also known as Final accepted manuscript or Post-print

Published under the following license:
CC BY-NC-ND

Please cite the original version:
Gómez Millán, G., El Assal, Z., Nieminen, K., Hellsten, S., Llorca, J., & Sixta, H. (2018). Fast furfural formation from xylose using solid acid catalysts assisted by a microwave reactor. *Fuel Processing Technology*, 182, 56-67. <https://doi.org/10.1016/j.fuproc.2018.10.013>

Fast furfural formation from xylose using solid acid catalysts assisted by a microwave reactor

Gerardo Gómez Millán^{*[a,b]}, Zouhair El Assal^[c], Kaarlo Nieminen^[a], Sanna Hellsten^[a], Jordi Llorca^[b], Herbert Sixta^{*[a]}

[a] G. Gómez Millán, DSc. K. Nieminen, DSc. S. Hellsten, Prof. H. Sixta
Department of Bioproducts and Biosystems
Aalto University
Vuorimiehentie 1, 02150 Espoo (Finland)
*E-mail: gerardo.gomezmillan@aalto.fi
herbert.sixta@aalto.fi

[b] G. Gómez Millán, Prof. J. Llorca
Department of Chemical Engineering, Institute of Energy Technologies and Barcelona Research Center in Multiscale Science and Engineering
Universitat Politècnica de Catalunya
Eduard Maristany 10-14, 08019 Barcelona (Spain)

[c] Z. El Assal
Department of Environmental and Chemical Engineering, Faculty of Technology
University of Oulu
P.O. Box 4300, 90014 Oulu (Finland)

Abstract: The production of furfural (FUR) from xylose was carried out using sulfated zirconia (SZ) on cordierite, alumina on cordierite and commercially-available polymeric solid catalysts (Amberlyst DT and Nafion NR40) to provide insights into the reaction pathways and kinetics for the dehydration of xylose in aqueous phase. Experiments conducted at three temperatures were investigated (170, 190 and 210 °C) in a stirred microwave-assisted batch reactor, which established the optimal conditions to obtain the highest FUR yield as well as extensive and fast xylose conversion. The maximum FUR yields obtained from xylose were 41 mol% when using SZ on cordierite in 2 min (at 210 °C), 43 mol% when using alumina on cordierite in 30 min (at 210 °C) and 48 mol% for an auto-catalyzed system in 60 min (at 210 °C). Based on the experimental results, a reaction mechanism was proposed considering the formation of an intermediate from xylose when solid acid catalysts were added. After five reusability cycles using SZ on cordierite, this catalyst can be regenerated with a similar performance and similar FUR yield on the 6th cycle.

Keywords: alumina; Amberlyst DT; furfural; Nafion NR40; sulfated zirconia; xylose

1. Introduction

Furfural (furan-2-carbaldehyde, FUR) is the dehydration product of xylose and other pentoses, C₅-sugars typically found in hemicellulose in lignocellulosic biomass. A wide range of FUR derivatives with high potential for applications has been identified. FUR is considered a selective solvent for organic compounds and serves as a building block for its hydrogenation to furfuryl alcohol, for components of P-series fuels or liquid alkanes, and in the manufacture of foundry resins [1-3]. Tetrahydrofuran and tetrahydrofurfuryl alcohol are the other two main chemicals obtained from FUR that have wide applications in the chemical industry. The rest of the FUR is employed in oil refining, pharmaceutical, plastics and agrochemical industries (as fungicide and nematicide) [4]. Although xylan and xylose have not yet been fully utilized in the paper industry, a significant amount of xylose, from the hydrolysis of woody biomass, is mixed with lignin-derived compounds and burned to provide process heat [5]. Therefore, valorization of these compounds offers a new economic approach for new ideas and new markets.

The commercial process for the production of FUR involves several environmental issues, such as toxic effluents derived from mineral acids (sulfuric or phosphoric acid) at temperatures of approximately 200 °C and the consumption of high stripping-steam to FUR ratios, especially related to important energy and environmental concerns regarding the fuel employed to generate the steam. Homogeneous acids (in the form of dilute aqueous solutions) achieve a one-step hemicellulose deconstruction and xylose dehydration in the same reactor. However, the utilization of these corrosive homogeneous mineral acids leads to challenges in product separation, equipment corrosion, mineral acid loss, high amounts of acidic and toxic waste, as well as a significant amount of side reactions that limit FUR yields to ca. 50% [6]. New methodologies based on the use of easily-separable solid catalysts including zeolites [7-14], aluminosilicates supported with metals [15], modified silica [16-23], alumina [12], zirconia [12,24] solid acids like layered zeolite Nu-6 [25], sulfonated graphenes [26], heteropolyacids [27-29], coated activated carbon [30] and resins [20,31,32] to yield xylose dehydration are currently being explored to improve FUR yields in a much more environmentally friendly and efficient industrial process.

Previous published literature has described the high catalytic activity of metal oxides in the dehydration of xylose into FUR. However, the hydrothermal stability of these materials has not been properly addressed. Furthermore, the reaction times to reach the highest FUR yields usually require from two [12] up to twenty hours [21,23,27-29,33]. Dias et al [29] studied various sulfated zirconias in the formation of FUR from xylose in an aqueous-toluene system at 160 °C in 4 h. They are able to identify a correlation of the catalytic activity with the sulfur content of the sulfated zirconia. Nevertheless, a significant amount of sulfur leaching is observed in the reusability tests. Zhang et al [34] used a $\text{SO}_4^{2-}/\text{ZrO}_2\text{-TiO}_2$ catalyst in a sugar mixture employing an aqueous-n-butanol biphasic system. The maximum FUR yield (48 mol%) was reached at 170 °C in 2 h. Even though the authors performed a reusability test, two cycles might not be enough to observe hydrothermal stability of the catalyst. Li et al [24] employed a $\text{SO}_4^{2-}/\text{TiO}_2\text{-ZrO}_2/\text{La}^{3+}$ catalyst in a biphasic system to form FUR from xylose. The highest FUR yield reported (3563 μmol of FUR/g of xylose) was reached in 12 h at 180 °C. However, the article lacks hydrothermal stability studies and the reusability potential of the metal oxide catalyst.

The ongoing discussion of the proper reaction mechanisms of FUR formation has generated proposals for different formation pathways under homogeneous and heterogeneous catalysis. O'Neill and co-workers claim that xylose could be isomerized to lyxose via adsorption onto the acidic active sites of ZSM-5 zeolite [8]. These steps would occur through the formation of the linear open chain of xylose molecules caused by the acid-catalyzed hydrolysis. On the other hand, Verma et al [35] proposed a mechanism via the formation of 2,5-anhydroxylose furanose cyclic intermediate using a sulfonated graphitic carbon nitride. Xylulose, a xylose isomer, has been under discussion as possible intermediate on FUR formation [36,37]. However, there is no conclusive information on either pathway.

In this work, we aimed to employ solid acid catalysts for the dehydration of xylose to produce FUR in short times (< 2 h). In addition, the kinetic model for this reaction was further investigated and a reaction mechanism is proposed for heterogeneously catalyzed systems. The hydrothermal stability of the solid catalysts is also addressed in the present paper. Due to their high acid site density [38,39], solid acid catalysts were developed (Al_2O_3 and $\text{ZrO}_2(\text{SO}_4^{2-})$ on cordierite) and compared to commercially available polymeric resins (Amberlyst DT and Nafion NR40). Their textural properties and acid site density were analyzed.

2. Materials and Methods

D-Xylose powder (99%, Sigma Aldrich) was used in the experiments without further purification. Formic acid (98%), levulinic acid (99%) and acetic acid (99%) were purchased from Sigma Aldrich and used for the preparation of calibration standards for HPLC analysis. Millipore grade water was used for preparing the solutions. Cordierite was obtained from Corning (Germany) and Disperal from Sasol Germany GmbH (Hamburg, Germany). Amberlyst DT was purchased from Rohm and Haas (France). Nafion NR40 beads were purchased from Ion Power GmbH (Germany).

2.1. Catalyst preparation

Pieces of cordierite (1-4 mm) were used as support. Sulfated zirconia (SZ, $\text{ZrO}_2(\text{SO}_4^{2-})$) and Al_2O_3 were prepared by impregnation of $\text{ZrOCl}_2 \cdot 8\text{H}_2\text{O}$ and boehmite suspensions as precursors over cordierite following the method of Ledesma *et al* [40]. The notation for SZ over cordierite is SZ_{cord} and for Al_2O_3 over cordierite is $\text{Al}_2\text{O}_{3\text{cord}}$. The resulting samples were dried at 105 °C and then calcined in air for 2-5 h to obtain the corresponding active oxides (SZ_{cord} at 500 °C; $\text{Al}_2\text{O}_{3\text{cord}}$ at 450 °C). Saez *et al* [38] found that cordierite presented no appreciable reactivity. The inclusion of cordierite in the catalyst preparation is to provide the catalyst a physical support for practical application. Reaction tests were conducted over Nafion NR40 and Amberlyst DT for the sake of comparison. Nafion NR40 was purified by treatment with hot hydrogen peroxide (5%) to remove organic impurities and soaked in 5 wt% hot hydrochloric acid to remove cations and exchange them by protons. It was dried overnight at 105 °C. Amberlyst DT was also dried overnight at 105 °C prior experimental tests.

2.2. Catalytic activity tests


Single component solution of D-xylose (186 mmol l^{-1}) were freshly prepared before the experiments. This specific xylose concentration was found to be in the prehydrolysate liquor from birch wood [41]. The first set of experiments was performed in the absence of solid acid catalysts. The second set of experiments was performed using 50 mg of $\text{Al}_2\text{O}_{3\text{cord}}$, SZ_{cord} , Amberlyst DT or Nafion NR40 as a catalyst. In a typical experiment, the glass reactor was loaded with 3 ml of the xylose solution and heated using a borosilicate glass reactor ($V = 10 \text{ cm}^3$) with magnetic stirring (600 min^{-1}) and microwave-assisted heating (Monowave 300, Anton Paar GmbH, Graz, Austria). After the reaction, the reactor was rapidly cooled to room temperature by utilizing compressed air. The highest temperature and the

longest reaction time studied at the present work were 210 °C and 180 min, respectively. After reaction, the solutions were tested for FUR yield, selectivity and xylose conversion at the reaction temperatures of 170, 190 and 210 °C with different reaction times in the range of 2-180 min.

In a typical experiment with solid acid catalyst, the glass reactor was loaded with 3 ml of an aqueous solution of 28 g l⁻¹ xylose and 50 mg of the catalyst. The reactor was placed in the microwave, heated to the set reaction temperature with an irradiation power of ≤ 850 W for maximum 1.5 min and kept at the reaction temperature for the set time. After the reaction, the reactor was rapidly cooled to room temperature by utilizing compressed air. For the reusability experiments, SZ_{cord} was collected after each use. It was washed with deionized water several times at room temperature and dried at 105 °C prior to reuse. All catalytic activity tests were performed in duplicate with a standard deviation below 10% (except for Nafion NR40, which its standard deviation is up to 33%).

2.3. Reaction mechanism

The kinetic modeling of xylose dehydration and FUR formation were based on the obtained experimental results following three possible reaction mechanisms. These reaction mechanisms were screened in order to find the optimal kinetic model explaining the xylose dehydration and FUR formation. Even though the reaction mechanism of FUR formation has been under discussion, these reaction mechanisms consider a pathway of FUR formation via an intermediate or xylose itself, a reaction mechanism did not consider a pathway solely via an intermediate. Using the xylose conversion data only in the modeling resulted in multiple equally well-fitting models with different mechanistic assumptions. The tested reaction mechanism considering the intermediate formation from xylose is as follows:

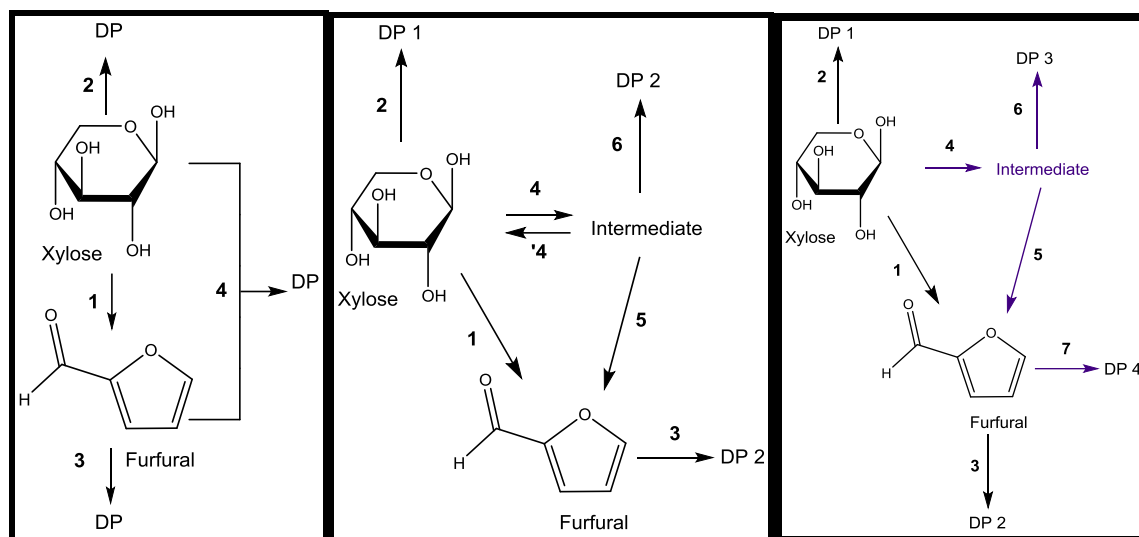

Scheme 1. FUR formation
with Direct Xylose
Decomposition

Scheme 2. FUR Formation with Side
Reaction between Intermediate and
FUR

Scheme 3. Parallel FUR Formation
with Side Reaction Decomposition

In the reaction model presented in scheme 1, xylose can be converted to FUR directly (k_1). In scheme 2, FUR can be formed from xylose either stepwise with an intermediate product (k_4+k_5), or via a direct or pseudo-direct reaction pathway (k_1). In the reaction model presented in scheme 3, FUR is formed stepwise via an intermediate (k_4+k_5) [41] or via a direct or pseudo-direct reaction pathway (k_1). The latter scheme proposes a parallel reaction model from the intermediate. The produced FUR further forms degradation products (DP). DP 2 is formed in the auto-catalyzed reaction and DP 4 formation is promoted by solid acid catalysts. Simultaneously, some fraction of xylose and intermediates (isomers or epimers of xylose) form also degradation products (DP 1 and DP 3). The HPLC analysis did not identify any significant amount from products originating from side reactions between xylose and FUR, as well as the isomerization of the intermediate back to xylose.

Previous kinetic studies have used either scheme 1 [42] or 2 [41,43,44] using homogeneous catalysts. Different formation pathways include isomerization of xylose to other pentoses such as lyxose and xylulose. Dias et al [29]

proposed a similar reaction mechanism for sulfated zirconia as scheme 2 shown in the present study, however there was no kinetic studies reported on the pathway of FUR formation from the intermediate.

3. Results and Discussion

3.1. Auto-catalyzed dehydration of xylose

Kinetic studies for auto-catalyzed xylose dehydration were performed at various reaction times at temperatures of 170, 190 and 210 °C. Figure 1 shows the FUR yield, xylose conversion and selectivity to FUR under these reaction conditions. The experimental tests can be considered as auto-catalyzed, since water is self-ionized to H^+ and OH^- ions that act as acid or base catalysts at the given temperature [45]. Later on, the carboxylic acids (formic, levulinic and acetic acid) or intermediates formed during the reaction, may have a catalytic effect [32,41,46]. The influence of the reaction temperature on the FUR yield and xylose conversion has been observed previously in similar work [37,47]. As Figure 1a displays, the FUR yield increased with reaction temperature up to 4 times from 170 to 190 °C after the first 60 min. When the reaction temperature was further increased from 190 to 210 °C, a 2-fold increase can be seen. It was observed that at the highest temperature investigated in the present study (210 °C) the FUR yield firstly increases and thereafter decreases, as the reaction time prolongs. The decrease of FUR yield in prolonged reaction time occurs due to decomposition and polymerization with humins production [48,49]. Under the present experimental conditions, the maximum FUR yield (48-49%) was reached after the first 60 min at 210 °C, which corresponds to a xylose conversion of 94% (Figure 1b) and a FUR selectivity of 52% (Figure 1c).

At reaction temperatures of 170 and 190 °C, no distinct FUR yield culmination point, with subsequent rapid decrease was perceived during the reaction time range investigated. However, a yield decrease similar to that observed at 210 °C could be possibly observed at lower reaction temperatures (170 and 190 °C) during prolonged reaction times. Nevertheless, the maximum yield unmistakably shifts to a longer reaction time with a decline of the reaction temperature. Furthermore, the FUR yield (and thus also the selectivity) decreases with decreasing the reaction temperature, this is in agreement with literature [50]. It is worth noting that the maximum selectivity to FUR observed in the auto-catalyzed conversion of xylose was 56-58% in the present studied range of reaction temperatures. These results agree with previously published papers [37].

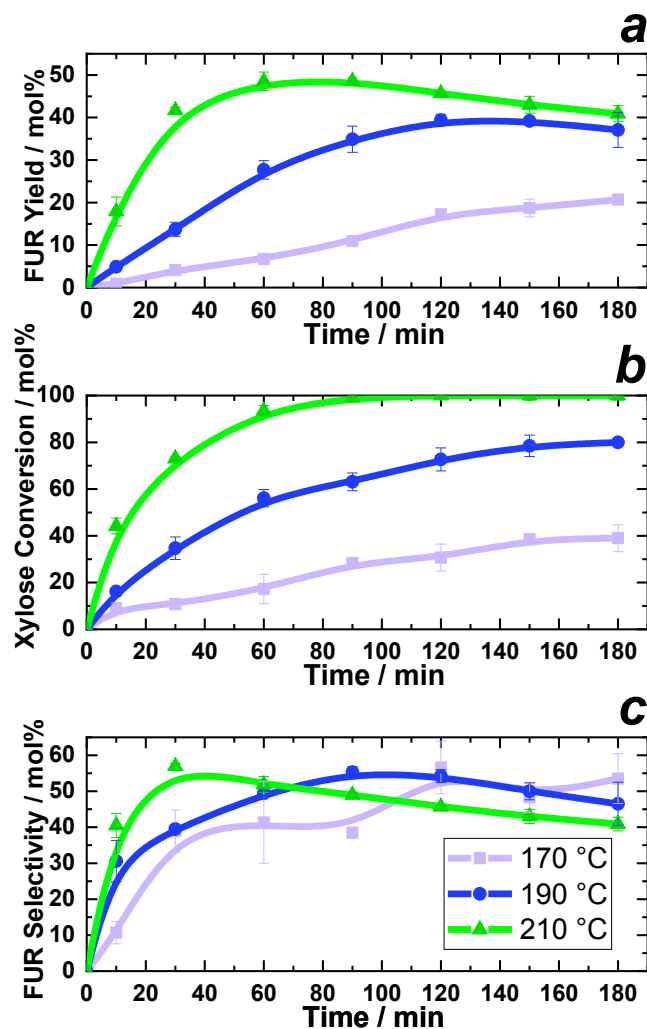


Figure 1. FUR yield (a), xylose conversion (b) and selectivity to FUR (c) at various reaction times during auto-catalyzed conversion of xylose 186 mmol l⁻¹ (purple square – 170 °C, blue circle – 190 °C, green triangle – 210 °C, lines are to guide the eye).

3.2. Catalyzed dehydration of xylose by solid acids

Figures 2a, 2b and 2c show the FUR yield, xylose conversion and selectivity to FUR at various reaction times at 170, 190 and 210 °C when Al₂O_{3cord} is present in the dehydration of xylose. For SZ_{cord}-catalyzed conversion of xylose Figures 2d, 2e and 2f show the FUR yield, xylose conversion and selectivity to FUR, respectively. Similarly to the auto-catalyzed process, the FUR yield and the xylose conversion are visibly influenced by the reaction temperature. When using Al₂O_{3cord}, the maximum FUR yield is clearly influenced by the reaction temperature: at 170 °C starts

from 26%, it increases furthermore up to 43% at 210 °C (Figure 2a). This is similar to the effect observed when adding SZ_{cord} , the maximum FUR yield increases from 36 to 41% when the reaction temperature is increased from 170 °C to 210 °C (Figure 2d). After the maximum FUR yield has been reached, selectivity decreases because the FUR formed reacts further, via condensation and resinification [12]. Hence, humin formation was observed. These FUR yield losses were observed at reaction temperatures of 190 and 210 °C.

Similarly as in the auto-catalyzed process, conversion of xylose to FUR needs relatively high temperatures (Figure 2b and 2e). When using Al_2O_{3cord} in the dehydration reaction of xylose, the maximum FUR yield (43%, Figure 2a) was reached in 30 min at 210 °C, corresponding to a xylose conversion of 91% (Figure 2b) and a FUR selectivity of 48% (Figure 2c). The maximum FUR yield (41%) was reached after 2 min at 210 °C during the SZ_{cord} -catalyzed reaction, corresponding to a xylose conversion of 96% (Figure 2e) and a FUR selectivity of 43% (Figure 2f). During the SZ_{cord} -catalyzed reaction, the maximum selectivity to FUR was 43% (at 210 °C in 2 min) in contrast to 57% (at 210 °C in 30 min) obtained in the auto-catalyzed reaction system. When comparing the present results with the catalyzed system using H_2SO_4 [37] and a xylose concentration of 196 mmol l⁻¹, the highest selectivity to FUR is 68% (at 180 °C in 5 min) and 65% (at 200 °C in 1 min, and at 220 °C in 2 min).

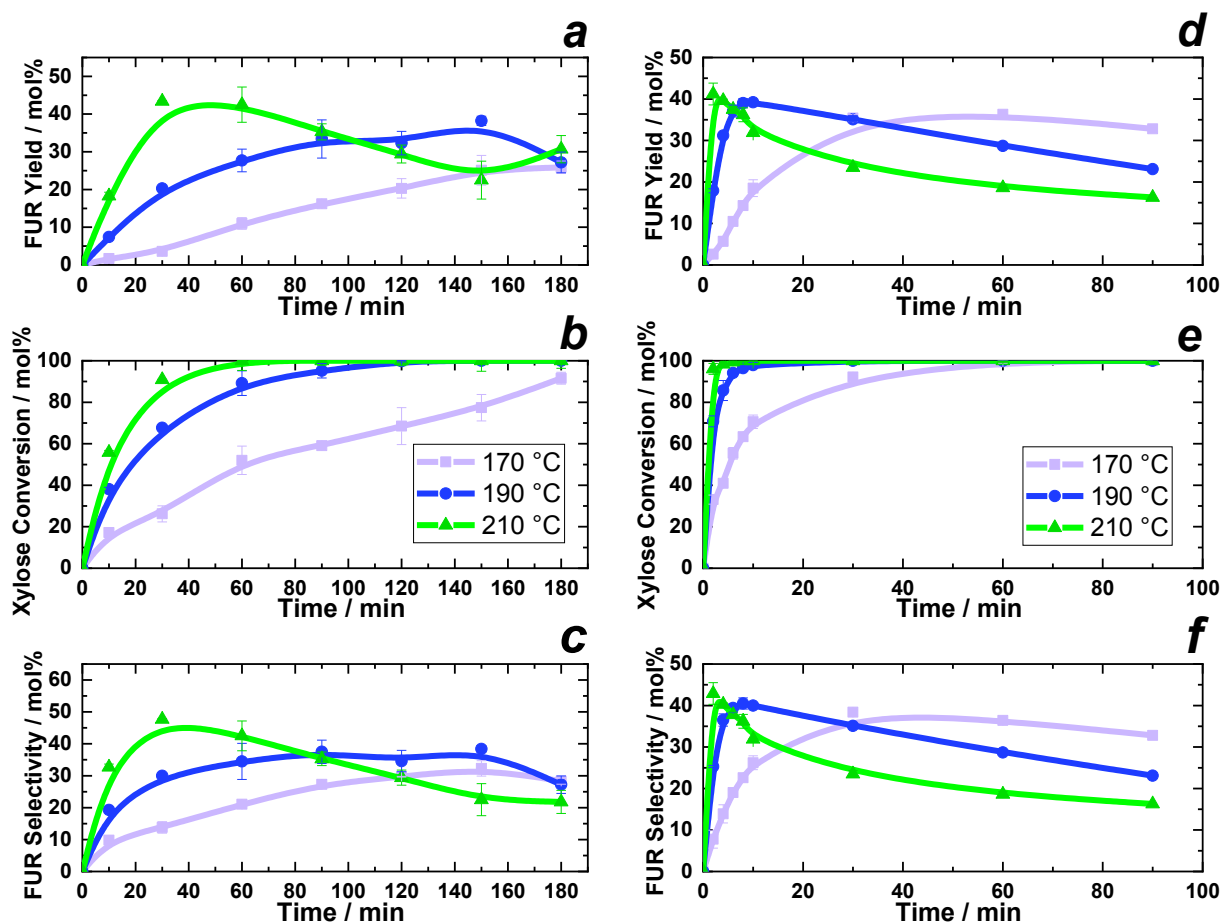


Figure 2. FUR yield (a,d), xylose conversion (b,e) and selectivity to FUR (c,f) at various reaction times during conversion of xylose 186 mmol l⁻¹ using Al₂O₃cord (a,b,c) and SZ_{cord} (d,e,f), respectively (purple square – 170 °C, blue circle – 190 °C, green triangle – 210 °C, lines are to guide the eye).

The FUR yield, xylose conversion and selectivity to FUR at various reaction times at 170 °C during conversion of xylose conducted with Amberlyst DT are shown in Figure S1. Amberlyst DT was only tested at 170 °C (maximum operational temperature) due to its limited hydrothermal stability as stated by the manufacturer. The maximum FUR yield (30%) was reached in 60 min at 170 °C with a xylose conversion of 70%.

The FUR yield, xylose conversion and selectivity to FUR at 170, 190 and 210 °C at various reaction times during xylose conversion conducted with Nafion NR40 are shown in Figure S2. In the same way that reaction temperature strongly influences FUR yield and xylose conversion in the auto-catalyzed process, the effect can be also observed

when adding Nafion NR40. When adding Nafion NR40 pellets to the aqueous system, the maximum FUR yield is determined by the reaction temperature: at 170 °C starts from 33%, furthermore it increases up to 41% at 210 °C. (Figure S2a). Due to the nature of the catalysts, the standard deviation increased at high reaction times and at high temperatures (>190 °C), even though the manufacturer guarantees its stability from 220 to 240 °C in aqueous systems. The catalysts clogged into each other making a barrier in the middle of the reactor. Therefore, the FUR and xylose concentration do not follow a smooth tendency. Nevertheless, xylose conversion behaves similarly to the auto-catalyzed system, since it requires longer reaction times to convert the same amount of xylose at a lower reaction temperature (Figure S2b). In the case of Nafion NR40, the maximum FUR yield (41%, Figure S2a) was reached in 8 min at 210 °C, resulting on a xylose conversion of 70% (Figure S2b) and a FUR selectivity of 60% (Figure S2c). During the Nafion NR40-catalyzed reaction, the maximum selectivity to FUR was 67% (at 210 °C in 2 min) in contrast to 43% (at 210 °C in 2 min) obtained in the SZ_{cord}-catalyzed reaction system, and 52% (at 210 °C in 60 min) in the auto-catalyzed reaction system.

Control experiments for cordierite were performed at 170 °C and 210 °C for 60 min. Xylose conversion, FUR yield and pH values can be considered comparable for systems in the presence of cordierite and in the auto-catalyzed system. In contrast, experiments employing 0.1 mol l⁻¹ H₂SO₄ were performed in earlier work [37]. These experiments show that the highest FUR yield (65%) is reached at 220 °C in 2 min. At 200 °C, the highest FUR yield (59%) is reached in 5 min. At 180 °C the highest FUR yield (55%) is reached in 25 min.

The xylulose formation, a possible key intermediate [36,51,52], was monitored by means of HPLC utilizing a pure xylulose solution as a reference. No detectable amounts of xylulose were observed in the initial xylose solutions. Under auto-catalyzed conditions at temperature reactions of 170-210 °C, xylulose formation was not detectable. This is in accordance with the low amount of xylulose yield (< 3 mol%) reported by Ershova et al [37] when employing a 196 mmol l⁻¹ xylose solution at reactions temperatures of 180, 200 and 220 °C.

Fig. S3a shows that the highest amount of xylulose (18 mol%) was formed when employing alumina as catalyst in the dehydration of xylose at 170 °C in 120 min. At this temperature, some amount of xylulose was still present even

after 3 h of treatment. When adding SZ_{cord} (Fig. S3b), 46 mol% was the highest amount of xylulose formed at 170 °C in 6 min. When the reaction temperature increased to 190 °C, the amount of yielded xylulose decreased (27 %). At 210 °C, 2% of xylulose was yielded in 2 min. The extent of xylulose formation was highest at the lowest reaction temperature (170 °C) used in the present paper.

Xylulose was not identified at any experimental temperature employed in the present paper when polymeric resins (Amberlyst DT and Nafion NR40) were added into the system.

3.3. Mathematical modeling

Assuming a sequence of predominantly pseudo-first order reactions, the reactions of the model are assumed to follow the rate equations for similar elementary reactions. When the reactions are carried out in a batch reactor, the component mass balance for scheme 1 (assuming that the k_3 rate constant describes that the reaction consumes equal amount of moles of xylose and FUR) are: equations 7 and 8;

$$\frac{d[Xylose]}{dt} = -(k_1 + k_2)[Xylose] - (k_4)[Xylose][FUR] \quad (7)$$

$$\frac{d[FUR]}{dt} = k_1[Xylose] - ((k_3)[FUR] + (k_4)[Xylose][FUR]) \quad (8)$$

for scheme 2 the component mass balance are shown in equations 9, 10 and 11;

$$\frac{d[Xylose]}{dt} = -(k_1 + k_2 + k_4)[Xylose] + k_{-4}[Intermediate] \quad (9)$$

$$\frac{d[Intermediate]}{dt} = k_4[Xylose] - (k_{-4} + k_5 + k_6)[Intermediate] \quad (10)$$

$$\frac{d[FUR]}{dt} = k_5[Intermediate] + k_1[Xylose] - k_3[FUR] \quad (11)$$

For scheme 3 for the auto-catalyzed system equations 12 and 13 show the component mass balance:

$$\frac{d[Xylose]}{dt} = -(k_1 + k_6)[Xylose] \quad (12)$$

$$\frac{d[FUR]}{dt} = k_1[Xylose] - k_3[FUR] \quad (13)$$

And for the solid acid-catalyzed system equations 14, 15 and 16:

$$\frac{d[Xylose]}{dt} = -(k_1 + k_2 + k_4)[Xylose] \quad (14)$$

$$\frac{d[Intermediate]}{dt} = k_4[Xylose] - (k_5 + k_6)[Intermediate] \quad (15)$$

$$\frac{d[FUR]}{dt} = k_1[Xylose] + k_5[Intermediate] - (k_3 + k_7)[FUR] \quad (16)$$

where $k_1, k_2, k_3, k_4, k_5, k_6, k_7$ are rate constants and $[Xylose], [Intermediate], [FUR]$ are concentrations (in mol l⁻¹) for xylose, intermediate and FUR, respectively.

The fittings of the kinetic models of the experimental results with pure xylose solution and solid acid catalysts corresponding to scheme 3 are shown in figures 3-5. The fittings show that the chemical intermediate concentration is strongly influenced by the reaction temperature and the presence of the solid acid catalysts. As it can be seen in figures 4 and 5, the concentration of the intermediate decreases when the reaction temperature increases. In the case of the Al₂O_{3cord} (Figure 5), the concentration of the chemical intermediate reaches up to 32 mmol l⁻¹ at 170 °C. When adding SZ_{cord}, this concentration increases up to 86 mmol l⁻¹ (Figure 4) also at 170 °C.

It has been reported previously that SZ_{cord} possesses Brønsted acid (BA) sites, while Al₂O_{3cord} presents a combination of BA and Lewis acid (LA) sites. BA are linked to direct pentose dehydration into FUR, and LA tend to isomerize pentoses into chemical intermediates, such as xylulose [12,20,36,53-55]. However, the discussion on the co-existence of BA and LA sites on the surface of SZ_{cord} and how to properly measure it still continues [56-58]. Furthermore, the discussion on the relationship between LA and BA sites effect on the dehydration mechanism is largely unclear [59]. The extent of sulfation on the SZ_{cord} was low (Table 5), which might favor the presence of LA [56], thus promoting reaction pathways with chemical intermediates, such as xylulose. For both systems employing solid acid catalysts (SZ_{cord} and Al₂O_{3cord}), the highest concentration of xylulose is reached at the lowest temperature (170 °C). This is in agreement with previous studies [36,37], which highlighted that the reaction of xylulose to FUR is favored at low temperatures in the presence of LA over the reaction of xylose to FUR. In contrast, at high temperatures LA catalysts lose the pathway via xylulose, due to gradual transformation of LA into BA, which can be

seen in Figure 4 and 5 where xylulose disappears as temperature increases. Their presence also involves the formation of degradation products such as carboxylic acids (formic, acetic and levulinic acid). These compounds were identified but not quantified. The figures corresponding to the models following scheme 1 and scheme 2 are displayed on Figures S4-S11.

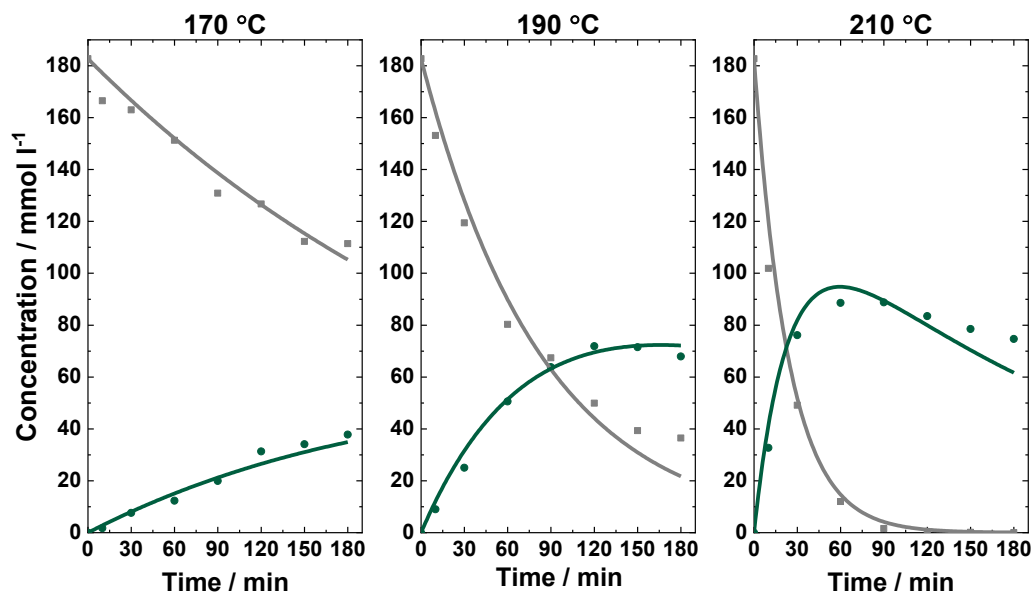


Figure 3. Scheme 3 and concentrations of FUR (green) and xylose (gray) at temperatures of 170, 190 and 210 °C in auto-catalyzed system. (Experimental-circle, modeled-solid lines).

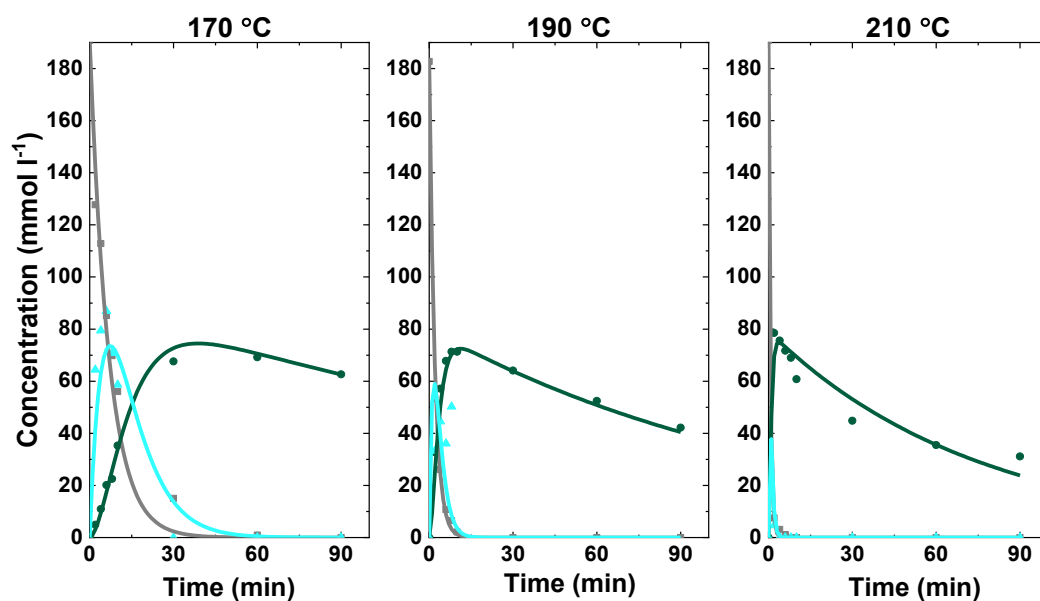


Figure 4. Scheme 3 and concentrations of FUR (green), xylose (grey) and xylulose (blue) at temperatures of 170, 190 and 210 °C with SZ_{cord}. (Experimental-circle, modeled-solid lines).

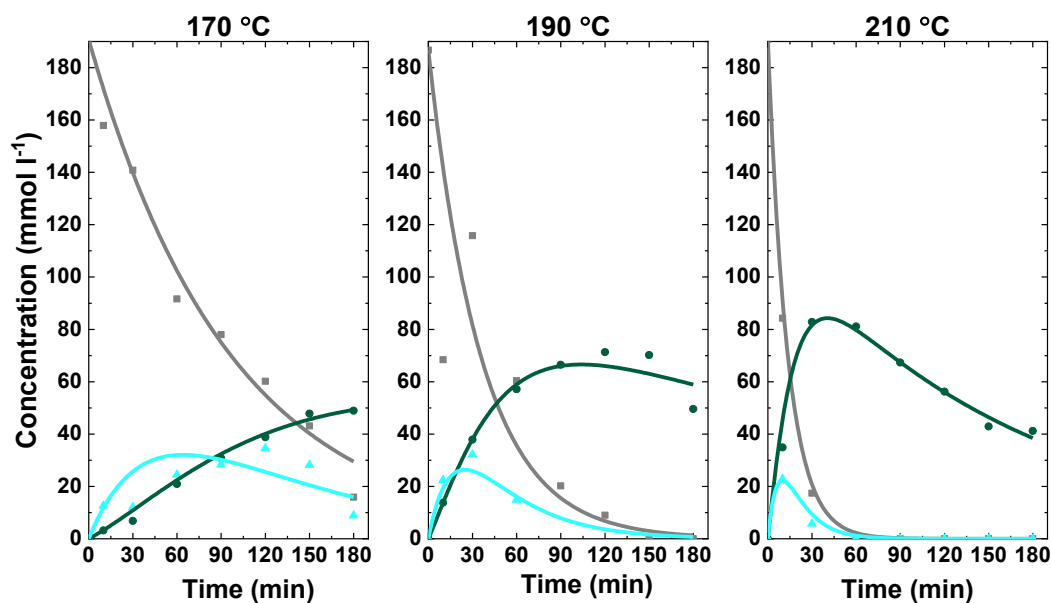


Figure 5. Scheme 3 and concentrations of FUR (green), xylose (grey) and xylulose (blue) at temperatures of 170, 190 and 210 °C with $\text{Al}_2\text{O}_{3\text{cord}}$. (Experimental-circle, modeled-solid lines).

3.4. Model fitting

The Figures 3-5 show that Scheme 3 predicts xylose and FUR concentrations properly. The models fit all the xylose conversion experimental data as well as FUR formation. The main difference between the three models is that scheme 3 includes a parallel reaction when the solid acid catalyst is added, thus describing the formation of an intermediate (xylulose). The best fitting of the model to experimental data was obtained considering a parallel pathway via an intermediate compound leading to the formation of FUR when using solid acid catalysts (Scheme 3) and a direct formation of FUR from xylose in the auto-catalyzed system.

In order to be able to elucidate relative contributions of individual steps (Table 1), the pre-exponential factor and the activation energy values were evaluated by fitting the models to the data. The rate constants were then calculated from the pre-exponential factor and the activation energy according to the Arrhenius equation. When SZ_{cord} and $\text{Al}_2\text{O}_{3\text{cord}}$ are added the temperature dependence of k_i is more pronounced, indicating that the reaction rates in the presence of solid acid catalyst are subtler to the reaction temperature. Tables 1-3 display the obtained kinetic parameters and the activation energy for each reaction step.

As Table 1 reveals, the rate constants for the xylose dehydration into FUR (k_1) increase as the temperature increases in the auto-catalyzed system. Similar to this, the rate constants for the decomposition of xylose (k_2) and FUR (k_3) also increase as the reaction temperature increases. The addition of SZ_{cord} and Al_2O_{3cord} as solid acid catalysts adds a reaction for the xylose isomerization (k_4), its dehydration to FUR (k_5) and the further decomposition products from the chemical intermediate (k_6) and from FUR (k_7). This observation is supported by the fact that sugar isomerization reactions are catalyzed by the presence of LA sites [36,37,53,59,60]. The addition of SZ_{cord} and Al_2O_{3cord} , increases the xylose decomposition (k_2). These results are in agreement with You *et al* [61], which confirms that LA sites are involved in the formation of humin from xylose dehydration. The rate constant for the decomposition of FUR (k_3, k_7) in the auto-catalyzed and catalyzed systems with SZ_{cord} and Al_2O_{3cord} are negligible. At the studied conditions when SZ_{cord} and Al_2O_{3cord} are added to the system, the formation of decomposition products is found to decrease in the order $k_6 > k_2 > k_7 > k_3$. This could be due to the introduction of BA sites, which increase the decomposition rate of pentoses [38].

Table 1. Kinetic rate constants k_i (min^{-1}) at each experimental temperature for auto-catalyzed and acid-catalyzed systems following Scheme 3.

T, (°C)	Solid acid catalysts	k_1	k_2	k_3	k_4	k_5	k_6	k_7
170	-	0.002	0.002	0.001				
190	-	0.007	0.005	0.002				
210	-	0.028	0.014	0.004				
170	SZ_{cord}	0.002	0.002	0.001	0.13	0.065	0.093	0.002
190	SZ_{cord}	0.007	0.005	0.002	0.54	0.43	0.64	0.004
210	SZ_{cord}	0.028	0.014	0.004	2.02	2.41	3.71	0.008

170	$\text{Al}_2\text{O}_{3\text{cord}}$	0.002	0.002	0.001	0.008	0.006	0.003	0.002
190	$\text{Al}_2\text{O}_{3\text{cord}}$	0.007	0.005	0.002	0.016	0.015	0.011	0.002
210	$\text{Al}_2\text{O}_{3\text{cord}}$	0.028	0.014	0.004	0.031	0.036	0.037	0.003

This is in line with the activation energy values presented in Table 3. The ratio of the reaction rate k_1/k_2 indicates that the dehydration of xylose is faster than the formation of decomposition products (Table 2). At the same time, the high ratio of k_1/k_3 shows that the reaction to FUR from xylose is much faster than the decomposition of FUR. When adding SZ_{cord} , the low ratio values of k_5/k_6 indicate that the intermediate decomposes faster than FUR is formed from it. This could be due to the introduction of LA sites, which are known to promote humin formation and decomposition into $\text{C}_1\text{-C}_3$ products [36,61]. Nevertheless, in the case of $\text{Al}_2\text{O}_{3\text{cord}}$, the opposite is true except at high temperatures (210 °C). This could be explained by the presence of LA sites that at high temperatures are transformed into BA sites [10,57]. Furthermore, the ratio k_1/k_4 demonstrates that the addition of solid acid catalysts, which present LA sites isomerize xylose into other pentoses (xylulose) as other authors have previously reported [12,20,36,55,60,62]. Furthermore, when SZ_{cord} is added to the reaction the ratio k_3/k_7 decreases as temperature increases. However, in the case of $\text{Al}_2\text{O}_{3\text{cord}}$, the rate of decomposition products forming from FUR in the auto-catalyzed system is faster than in the solid acid-catalyzed system. Nevertheless, k_3 and k_7 values are negligible as Table 1 shows.

Table 2. Ratio of selected kinetic rate constants at each experimental temperature for auto-catalyzed and solid acid-catalyzed systems following Scheme 3.

T, (°C)	Solid acid	k_1/k_2	k_1/k_3	k_5/k_6	k_1/k_4	k_3/k_7
170	-	1.07	1.23			
190	-	1.51	2.84			

210	-	2.11	6.33			
170	SZ _{cord}	1.07	1.23	0.70	0.01	0.81
190	SZ _{cord}	1.51	2.84	0.67	0.01	0.66
210	SZ _{cord}	2.11	6.33	0.65	0.01	0.54
170	Al ₂ O _{3cord}	1.07	1.23	1.77	0.21	0.62
190	Al ₂ O _{3cord}	1.51	2.84	1.36	0.44	1.09
210	Al ₂ O _{3cord}	2.11	6.33	0.97	0.92	1.73

The frequency factors and activation energy values for each reaction step are shown in Table 3. For comparison reasons, some published data related to similar reaction steps are also shown in Table S1. To the authors' knowledge, the frequency factors and activation energy values of xylose isomerization to the intermediate, to FUR and degradation products formation from the intermediate following scheme 3 have not been previously reported in literature for neither auto-catalyzed nor catalyzed reactions with solid acid catalysts present. In comparison to the auto-catalyzed system, when using SZ_{cord} and Al₂O_{3cord} in the system the activation energy values increased. The activation energy calculated when employing SZ_{cord} and Al₂O_{3cord} in the present study are higher than those published before the present study. These divergences between data could be possibly explained by either implementation of simplified reaction mechanism [2,53,63-66] or utilization of subcritical and supercritical reaction condition in earlier studies [67].

Table 3. Frequency factors ($A_{ref,i}$ min⁻¹) and activation energy values (E_{ai} , kJ mol⁻¹) for the kinetic model proposed in scheme 3; auto-catalyzed system, SZ_{cord}- and Al₂O_{3cord}-catalyzed system.

Scheme		$A_{ref,i}(\text{auto-})$	$E_{ai}(\text{auto-})$	$A_{ref,i}(SZ_{cord})$	$E_{ai}(SZ_{cord})$	$A_{ref,i}(Al_2O_{3cord})$	$E_{ai}(Al_2O_{3cord})$
Number		catalyzed)	catalyzed)				
3	(1)	$3.2 \times 10^{+11}$	121				
	(2)	$1.9 \times 10^{+9}$	103				
	(3)	2900	53.7				
	(4)			$3.42 \times 10^{+13}$	122	$1.92 \times 10^{+5}$	63
	(5)			$5.85 \times 10^{+17}$	161	$3.8 \times 10^{+7}$	83
	(6)			$1.99 \times 10^{+18}$	164	$3.54 \times 10^{+10}$	111
	(7)			$7.02 \times 10^{+5}$	73	0.031	10

Confidence intervals for the kinetic parameters in Table 3 are shown in Table S2 in the Supplementary Information. As expected, the ranges of the intervals are significant; the frequency factors vary with several orders of magnitude, which is in agreement with the exponential nature of the quantity. For reaction (7) it was not possible to calculate the confidence interval for the activation energy in the case of Al_2O_{3cord} due to the proximity of zero.

Reaction rate constants, frequency factors and activation energy values when using Nafion NR40 can be seen in Tables S3, S4 and S5. Frequency factors and activation energy values for the kinetic models (scheme 1 and 2); in the auto-catalyzed system and when using SZ_{cord} and Al_2O_{3cord} can be seen in Table S7. Due to the absence of xylulose when the polymeric resins were employed, scheme S1 shows the model use to fit the experimental data when using the resins in the present system.

3.5. Catalyst characterization

Solid acid catalysts before and after hydrothermal reaction were characterized based on the highest FUR yield reached at the three selected temperatures (170, 190 and 210 °C). The notation for SZ_{cord} and Al_2O_{3cord} after hydrothermal reaction at 170 °C includes a hyphen, e.g. $SZ_{cord-170}$ (where the highest FUR yield was reached).

3.5.1. Morphology of the solid acid catalysts

Fig. 6 shows, as an example, the scanning electron micrographs of $Al_2O_{3cord-fresh}$ and $Al_2O_{3cord-210}$ catalyst samples. On the $Al_2O_{3cord-fresh}$ sample, Fig. 6(a), the alumina plates can be seen on the surface. Fig. 6(c) corresponds to $Al_2O_{3cord-210}$ on cordierite sample (210 °C after 30 min). Fig. 6(b,d) correspond to $Al_2O_{3cord-fresh}$ and $Al_2O_{3cord-210}$ on cordierite sample at a higher magnification. It can be seen on Fig. 6(c,d) humin formation on the surface of the metal oxide catalyst samples (see spheres marked with arrows).

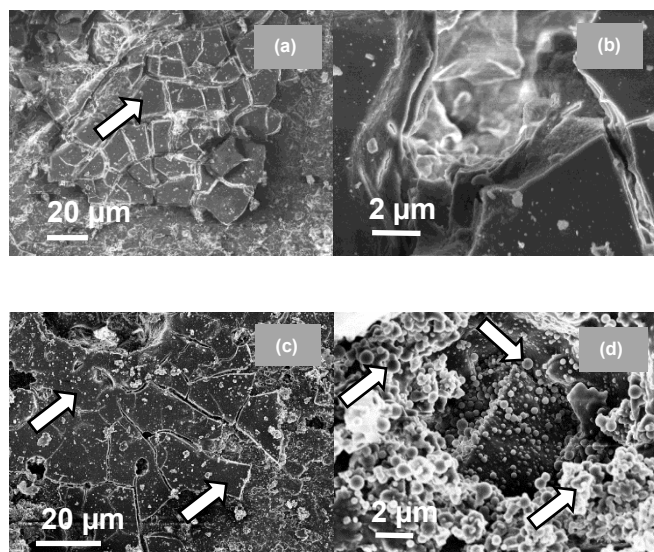


Figure 6. SEM images of (a,b) Al_2O_{3cord} , (c,d) $Al_2O_{3cord-210}$.

SZ_{cord} can be seen on Fig. 7(a,b), the SEM images show similitude of the SZ_{cord} characteristically cylindrical-like structure as reported by Al-Hazmi and Apblett [68]. $SZ_{cord-210}$ on cordierite catalyst sample is shown on Fig. 7(c,d) after the hydrothermal reaction at 210 °C for 2 min. On the surface of the spent samples appeared spheres (marked by arrows in Fig. 7(c,d)), which are humins formed in the hydrothermal reaction.

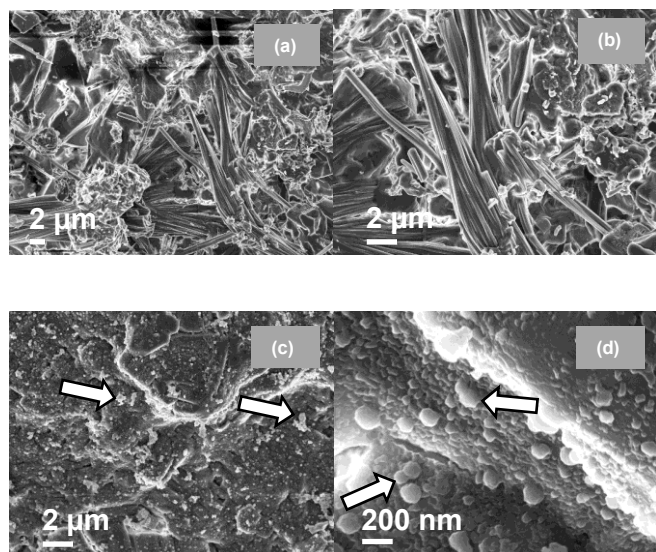


Figure 7. SEM images of (a,b) SZ_{cord} , (c,d) $SZ_{cord-210}$.

SEM images of Nafion NR40_{fresh} and Nafion NR40₂₁₀, Amberlyst DT_{fresh} and Amberlyst DT₁₇₀, as well as $SZ_{cord-170}$, $SZ_{cord-190}$ and $SZ_{cord-reused}$ can be seen in Figures S12, S13 and S14, respectively. The structure of these spherical particles 2-3 μm in size agree with the findings of Van Zandvoort et al [48], who studied humin formation from acid-catalyzed dehydration of xylose under standard reaction conditions of 180 °C, 1 M solution of sugar and 0.01 M H_2SO_4 . These insoluble polymeric structures are formed by aqueous acidic media of most lignocellulosic biomass valorization processes [2,59,69]. The formation of carbonaceous deposits is detrimental to the reaction as can be seen in Figures 1 and 2.

3.5.2. N_2 -sorption

The BET (Brunauer-Emmett-Teller) specific surface areas and pore volumes obtained by the nitrogen physisorption are compiled in Table 4. Both polymeric resins (Amberlyst DT and Nafion NR40) show low BET specific surface area ($0.2 m^2 g^{-1}$), but Al_2O_{3cord} sample exhibits a higher surface area ($11.8 m^2 g^{-1}$). SZ_{cord} sample also shows a low BET of $0.8 m^2 g^{-1}$ (as reported by Casanovas *et al* [70] the A_{BET} of the support (cordierite) is $0.1 m^2 g^{-1}$). The pore width distributions shown in Figure S15 reveal a narrow pore width of approximately 45 Å in Al_2O_{3cord} . These pores occupy a large part of the total pore volume in Al_2O_{3cord} . There are three other broader pore widths at 115, 153 and 311 Å with high pore volumes. There can be seen two similar pore width distributions in SZ_{cord} at 193 and 310 Å with high

pore volumes. The pore volume for both commercial polymeric resins is below $4 \times 10^{-5} \text{ cm}^3 \text{ g}^{-1}$. The pore width distributions of Amberlyst DT reveal a broad pore width of approximately 604 Å. Nafion NR40 shows a small pore width at 513 Å.

Table 4. Textural properties of solid acid catalysts (i.e., BET (A_{BET}), Pore volume (V_p) and Pore diameter (d_p)).

Catalysts	$A_{\text{BET}} (\text{m}^2 \text{ g}^{-1})$	$V_p (\text{cm}^3 \text{ g}^{-1})$	$d_p (\text{nm})$
$\text{Al}_2\text{O}_{3\text{cord}}$	11.8	10^{-2}	4.4
SZ_{cord}	0.8	10^{-3}	5.0
Nafion NR40	0.2	4×10^{-5}	1.4
Amberlyst DT	0.2	10^{-4}	1.1

As reported by other researchers [59,71], a large surface area is preferable to ease accessibility of xylose (for adsorption and further dehydration purposes). The effect of a higher A_{BET} , hence a higher amount of active sites available in the reaction to dehydrate xylose, in the case of $\text{Al}_2\text{O}_{3\text{cord}}$ could be observed in Figure 2 with a higher selectivity (48%) in comparison to SZ_{cord} (43%). The pore widths of solid acid catalysts used in the present study are larger than optimal pore widths reported previously to provide accessibility for xylose and FUR molecules [71].

3.6. Catalyst stability

3.6.1. NH_3 -TPD

To obtain insight into the catalytic activity tendency, Table 5 shows the total density of acid sites determined by temperature-programmed desorption profile of NH_3 (NH_3 -TPD). Even though there are continuing discussions about the acidity of SZ [72,73] and Al_2O_3 , clearly, the acidity of $\text{Al}_2\text{O}_{3\text{cord}}$ ($137.2 \mu\text{mol of NH}_3 \text{ g}^{-1}$) was much higher than that of SZ_{cord} ($38.4 \mu\text{mol of NH}_3 \text{ g}^{-1}$). This comparison agrees with that reported by Saez et al [38], which confirms that $\text{Al}_2\text{O}_{3\text{cord}}$ have higher total acid sites than SZ_{cord} . This is in contrast with the acid site density of SZ and Al_2O_3 reported by other researchers [2,12,74], the reported values could be due to the synthesis method employed.

After hydrothermal reaction at 210 °C in 30 min, $\text{Al}_2\text{O}_{3\text{cord}}$ lost more than half of its total acid sites ($41.9 \mu\text{mol of NH}_3 \text{ g}^{-1}$), as well as SZ_{cord} after hydrothermal reaction at 190 °C in 10 min ($27.8 \mu\text{mol of NH}_3 \text{ g}^{-1}$). It is assumed that the loss of acid sites under experimental conditions is due to high pressure (>12 bar) and hydrothermal conditions in the reactor.

Table 5. Total acid site density of calcined catalysts determined by temperature-programmed desorption (TPD) of NH_3 from 100 °C to 600 °C.

catalyst	total acid sites ($\mu\text{mol of NH}_3 \text{ g}^{-1}$)
$\text{Al}_2\text{O}_{3\text{cord}}$	137.2
$\text{Al}_2\text{O}_{3\text{cord-210}}$	41.9
SZ_{cord}	38.4
$\text{SZ}_{\text{cord-190}}$	27.8

The ion exchange capacities of the polymeric resins were verified by back-titration following the method reported by Goertzen *et al* [75]. Table S6 shows that Amberlyst DT (a macroreticular, sulfonic acid polymeric catalyst) has three times more acid sites (3.1 meq g^{-1}) than Nafion NR40 in bead form (1.0 meq g^{-1}). According to the manufacturer, Nafion NR40 in bead-form has an ion exchange capacity of 1.0 meq g^{-1} . Amberlyst DT (a macroreticular, sulfonic acid polymeric catalyst) has a concentration of acid sites of $\geq 3.1 \text{ meq g}^{-1}$.

3.6.2. XPS

Apart from the thorough microstructural analysis of the above samples, a detailed XPS analysis was performed to get a deeper insight about the surface composition of the materials. In Table 6 the binding energy values and surface atomic composition of metal oxides before and after hydrothermal reaction are shown.

Table 6. XPS data of SZ_{cord} and Al₂O_{3cord} on cordierite before and after the hydrothermal reaction at different temperatures.

Sample	Name	Binding Energy (eV)	Atomic conc., %
SZ _{cord-fresh}	O 1s	531.9	52.9
	C 1s	279.7	29.4
	S 2p	168.5	15.1
	Zr 3d	182.4	2.7
SZ _{cord-170}	O 1s	531.7	23.6
	C 1s	284.2	75.8
	S 2p	169.0	0.1
	Zr 3d	182.3	0.5
SZ _{cord-190}	O 1s	531.8	30.4
	C 1s	284.3	67.1
	S 2p	168.3	0.7
	Zr 3d	182.3	1.8
SZ _{cord-210}	O 1s	531.7	36.2
	C 1s	283.8	60.6
	S 2p	168.2	0.7

	Zr 3d	182.4	2.5
SZ _{cord-reused}	O 1s	532.2	48.8
	C 1s	284.2	48.9
	Zr 3d	182.4	2.3
Al ₂ O _{3cord-fresh}	O 1s	528.3	43.8
	C 1s	281.7	23.6
	Al 2s	118.7	19.5
	Mg 2p	48.4	13.0
Al ₂ O _{3cord-210}	O 1s	527.6	26.2
	C 1s	283.5	59.0
	Al 2s	118.7	1.8
	Mg 2p	49.9	13.0

The amount of sulphur at the surface in the sample SZ_{fresh} is 15%, and the amount of sulphur in the samples SZ₁₇₀, SZ₁₉₀ and SZ₂₁₀, is 0.1, 0.7 and 0.7, respectively. For the sample SZ_{reused} there was no measurable sulphur traces. It is inferred from Tables 5 and 6 that there is leaching of the acid sites of both Al₂O_{3cord} and SZ_{cord}. This means that the acid sites found in the fresh sample have leached out into the aqueous solution under the reaction conditions presented in this paper. It is also shown that the atomic concentration of C is lower on the surface of the fresh sample (29%) than the atomic concentration of C on the spent samples SZ_{cord-170} (76%), SZ_{cord-190} (67%), SZ_{cord-210} (61%) and SZ_{cord-reused} (49%). This means that there is carbon deposition on the surface of the catalyst after hydrothermal reaction, in accordance to the humins imaged by SEM (Figures 7c and 7d).

The amount of aluminum at the surface in the sample $\text{Al}_2\text{O}_{3\text{cord-fresh}}$ is 19.5%, and the amount of aluminum in the sample $\text{Al}_2\text{O}_{3\text{cord-210}}$ is 1.8%. This shows the leaching of the acid sites found in the fresh sample have also leached out from the catalyst into the aqueous solution. The sample of $\text{Al}_2\text{O}_{3\text{cord-fresh}}$ contains a lower C amount (24%) than the sample $\text{Al}_2\text{O}_{3\text{cord-210}}$ after hydrothermal reaction (59%). This also evidences the formation of carbon deposits on the surface (Figures 6c and 6d) of the catalyst after hydrothermal reaction.

Table S7 shows the binding energy and the atomic concentration percentages of Nafion NR40 before and after hydrothermal reaction at 210 °C, and Amberlyst DT before and after hydrothermal reaction at 170 °C. Under those conditions, both catalysts suffer a sulphur loss. In addition, Amberlyst DT loses Cl and Nafion NR 40 loses F. Hence, leaching of acid sites under these conditions was seen from all solid acid catalysts tested.

Figures S16 and S17 show the X-ray photoelectron spectra of SZ_{cord} and $\text{Al}_2\text{O}_{3\text{cord}}$, respectively, before and after hydrothermal reactions at different temperatures. Figures S18 and S19 show the X-ray photoelectron spectra of Amberlyst DT and Nafion NR40, respectively, before and after hydrothermal treatment. Figures S20 and S21 show the TCD of SZ_{cord} and $\text{Al}_2\text{O}_{3\text{cord}}$ before and after hydrothermal reaction.

In the dehydration of xylose, the degradation of acid concentration, the leaching of S and the accumulation of by-products are the main factors that cause the deactivation of the catalyst. The results shown in Tables 5 and 6 from samples SZ_{cord} and $\text{Al}_2\text{O}_{3\text{cord}}$ before and after hydrothermal reaction correlate with the catalytic activity tests in Figure 1 and 2 and the models shown in Figures 3-5. Under the above-mentioned experimental conditions FUR, once it is formed, it decomposes as well as the xylose. The decomposition products evolve forming humins on the surface of the catalysts (Figure 6 and 7), which is obviously detrimental to the reaction.

Besides, the proposed kinetic model (Scheme 3) was applied also to a purely homogeneous catalyzed dehydration reaction (employing H_2SO_4) in order to exclude the effect of leaching acidic species on the reaction mechanism of SZ_{cord} (this information can be found in the Supplementary Information). The proposed kinetic model simulates heterogeneous- and homogeneous-catalyzed systems very well (Figure S22 and S23, Table S1 and S2). Furthermore,

the acid content in the sulfuric acid-catalyzed reaction (Figure S24) was almost one order of magnitude higher, both xylose concentration and FUR formation can be simulated with the same kinetic model (Figure S4).

3.7. Reusability

The stability of the SZ_{cord} under reaction conditions was investigated by employing this catalyst in a series of xylose dehydration reactions. Prior to each cycle, the SZ_{cord} was washed with deionized water and dried at 105 °C. Figure 8 shows five consecutive reaction runs of SZ_{cord} at 190 °C in 9 min. After this, the catalyst was washed, dried at 105 °C, calcined and impregnated again with 1 M H₂SO₄ (cycle 6).

After 5 cycles, the catalytic activity of the reused catalyst decreased from 38% to 7%, as well as the conversion of xylose (from 97% to 37%). At the same time, the activity of the catalyst can be recovered by calcination and a FUR yield of 39% is obtained again. These results are in accordance with the XPS results, since the catalytic activity of the reused catalysts decreased in each cycle without regeneration. This result indicates that the observed progressive catalyst deactivation might be related to the accumulation of insoluble organic matter, which could be blocking the surface of the catalyst, hence leading to disabled acid sites. The catalyst deactivation includes also leaching of the active sites (Table 6).

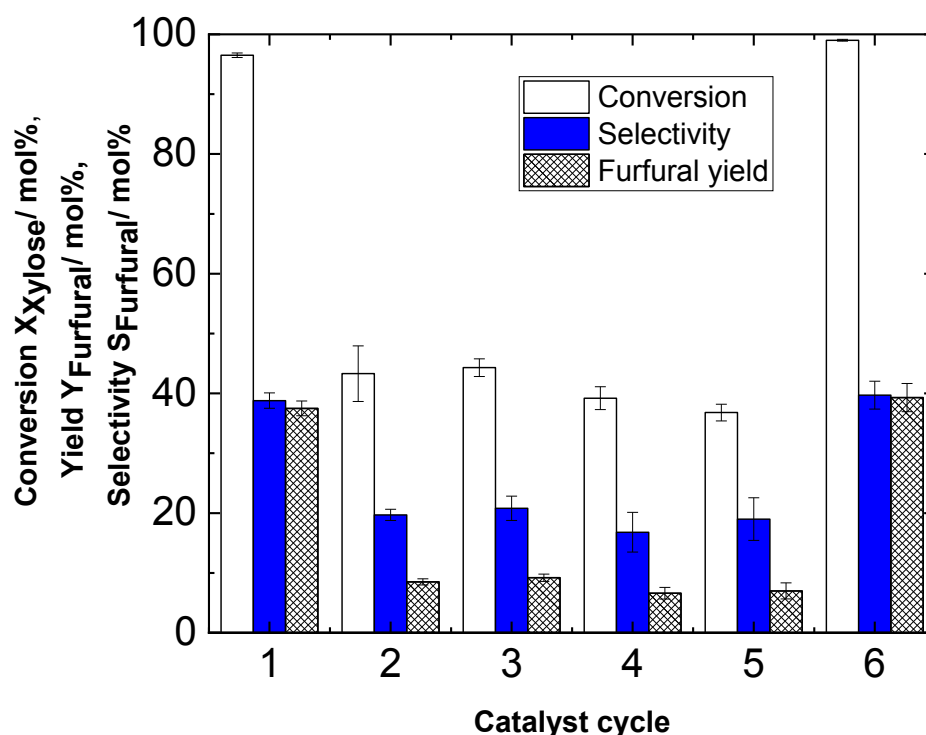


Figure 8. Reusability of SZ_{cord} for the dehydration of xylose to FUR using 50 mg of catalyst at 190 °C for 9 min (xylose conversion (white bar), FUR yield (blue bar) and selectivity to FUR (striped bar)).

4. Conclusions

A kinetic model for the auto-catalyzed and solid acid-catalyzed decomposition of xylose using SZ_{cord} , Al_2O_{3cord} on cordierite and Nafion NR40 at temperatures from 170 to 210 °C in aqueous phase was developed. Reaction rate constants for xylose and FUR decomposition were also determined in the temperature range of 170 to 210 °C. The major product of auto-catalyzed and solid acid-catalyzed xylose dehydration was FUR, the maximum mole fraction yield of which was 49% in 60 min at 210 °C. When using SZ_{cord} , the fastest time to reach the maximum mole fraction yield (41%) was in 2 min (at 210 °C). When adding Al_2O_{3cord} , the fastest time to reach the maximum mole fraction yield (43%) was in 30 min (at 210 °C). When adding Nafion NR40 and Amberlyst DT, the maximum mole fraction yield of FUR was 41% in 8 min at 210 °C and 30% in 60 min at 170 °C, respectively. Under the experimental conditions used, leaching of S, F, Cl was evidenced from SZ_{cord} , Nafion NR40 and Amberlyst DT, respectively. Besides, the acid site density of spent samples shows lower values than those of fresh catalysts. It was also seen deposition of C on

the surface of samples after hydrothermal reaction, which means that humins were formed on the solid acid catalysts, affecting the solid acid catalysts' performance.

There was no xylulose formation detected under auto-catalyzed conditions, xylulose was only formed when adding SZ_{cord} and Al₂O_{3cord}. This could be due to the presence of Lewis acid sites contained in the solid acid catalysts.

Overall, hydrothermal stability should be further improved in future work, as well as their acid site density. In addition, it is crucial to avoid the decomposition of FUR once it is formed, either by a secondary process such as nitrogen-stripping or on-site extraction systems such as organic solvents included in a bi-phasic set-up.

Acknowledgements

This research has been done in collaboration with Stora Enso and funded through Erasmus Mundus Joint Doctoral Programme SELECT+, the support of which is gratefully acknowledged. G.G.M. was supported also by CIMO (Centre for International Mobility Finland) and by CONACyT (the Mexican National Council of Science and Technology). The authors are also grateful for the support of the staff at the Department of Bioproducts and Biosystems at Aalto University and the Institute of Energy Technologies in the Technical University of Catalonia, especially to Rita Hatakka (at Aalto University), Albert Casanovas and Lluís Soler (at UPC). Satu Ojala supported this research with NH₃-TPD analysis at the University of Oulu, Finland.

References

- [1] J.N. Chheda, G.W. Huber, J.A. Dumesic, Liquid-Phase Catalytic Processing of Biomass-Derived Oxygenated Hydrocarbons to Fuels and Chemicals, *Angewandte Chemie International Edition*. 46 (2007) 7164-7183.
- [2] R. Weingarten, J. Cho, J. Conner Wm.Curtis, G.W. Huber, Kinetics of furfural production by dehydration of xylose in a biphasic reactor with microwave heating, *Green Chem.* 12 (2010) 1423-1429.
- [3] J. Carlos Serrano-Ruiz, J.A. Dumesic, Catalytic upgrading of lactic acid to fuels and chemicals by dehydration/hydrogenation and C-C coupling reactions, *Green Chem.* 11 (2009) 1101-1104.
- [4] K.J. Zeitsch, 14. Applications of furfural, in: K.J. Zeitsch (Ed.), *The chemistry and technology of furfural and its many by-products*, Elsevier B.V., 2000, pp. 98-103.
- [5] L. Yang, J. Su, S. Carl, J.G. Lynam, X. Yang, H. Lin, Catalytic conversion of hemicellulosic biomass to lactic acid in pH neutral aqueous phase media, *Applied Catalysis B: Environmental*. 162 (2015) 149-157.

- [6] A.S. Mamman, J. Lee, Y. Kim, I.T. Hwang, N. Park, Y.K. Hwang, et al., Furfural: Hemicellulose/xylose-derived biochemical, Biofuels, Bioproducts and Biorefining. 2 (2008) 438-454.
- [7] C. Moreau, R. Durand, D. Peyron, J. Duhamet, P. Rivalier, Selective preparation of furfural from xylose over microporous solid acid catalysts, Industrial Crops and Products. 7 (1998) 95-99.
- [8] R. O'Neill, M.N. Ahmad, L. Vanoye, F. Aiouache, Kinetics of Aqueous Phase Dehydration of Xylose into Furfural Catalyzed by ZSM-5 Zeolite, Ind Eng Chem Res. 48 (2009) 4300-4306.
- [9] R. Sahu, P.L. Dhepe, A One-Pot Method for the Selective Conversion of Hemicellulose from Crop Waste into C5 Sugars and Furfural by Using Solid Acid Catalysts, ChemSusChem. 5 (2012) 751-761.
- [10] S. Lima, A. Fernandes, M.M. Antunes, M. Pillinger, F. Ribeiro, A.A. Valente, Dehydration of Xylose into Furfural in the Presence of Crystalline Microporous Silicoaluminophosphates, Catalysis Letters. 135 (2010) 41-47.
- [11] S. Lima, M.M. Antunes, A. Fernandes, M. Pillinger, M.F. Ribeiro, A.A. Valente, Catalytic cyclodehydration of xylose to furfural in the presence of zeolite H-Beta and a micro/mesoporous Beta/TUD-1 composite material, Applied Catalysis A: General. 388 (2010) 141-148.
- [12] R. Weingarten, G.A. Tompsett, W.C. Conner Jr., G.W. Huber, Design of solid acid catalysts for aqueous-phase dehydration of carbohydrates: The role of Lewis and Brønsted acid sites, Journal of Catalysis. 279 (2011) 174-182.
- [13] L.R. Ferreira, S. Lima, P. Neves, M.M. Antunes, S.M. Rocha, M. Pillinger, et al., Aqueous phase reactions of pentoses in the presence of nanocrystalline zeolite beta: Identification of by-products and kinetic modelling, Chem. Eng. J. 215-216 (2013) 772-783.
- [14] E.I. Gürbüz, J.M.R. Gallo, D.M. Alonso, S.G. Wettstein, W.Y. Lim, J.A. Dumesic, Conversion of Hemicellulose into Furfural Using Solid Acid Catalysts in γ -Valerolactone, Angewandte Chemie International Edition. 52 (2013) 1270-1274.
- [15] A. Yepez, A. Garcia, M.S. Climent, A.A. Romero, R. Luque, Catalytic conversion of starch into valuable furan derivatives using supported metal nanoparticles on mesoporous aluminosilicate materials, Catal. Sci. Technol. 4 (2014) 428-434.
- [16] M.J.C. Molina, M.L. Granados, A. Gervasini, P. Carniti, Exploitation of niobium oxide effective acidity for xylose dehydration to furfural, Catalysis Today. 254 (2015) 90-98.
- [17] G.H. Jeong, E.G. Kim, S.B. Kim, E.D. Park, S.W. Kim, Fabrication of sulfonic acid modified mesoporous silica shells and their catalytic performance with dehydration reaction of d-xylose into furfural, Microporous and Mesoporous Materials. 144 (2011) 134-139.
- [18] S. Kaiprommarat, S. Kongparakul, P. Reubroycharoen, G. Guan, C. Samart, Highly efficient sulfonic MCM-41 catalyst for furfural production: Furan-based biofuel agent, Fuel. 174 (2016) 189-196.
- [19] I. Agirrezabal-Telleria, J. Requies, M.B. Güemez, P.L. Arias, Pore size tuning of functionalized SBA-15 catalysts for the selective production of furfural from xylose, Applied Catalysis B: Environmental. 115-116 (2012) 169-178.
- [20] I. Agirrezabal-Telleria, C. García-Sancho, P. Maireles-Torres, P.L. Arias, Dehydration of xylose to furfural using a Lewis or Brønsted acid catalyst and N₂ stripping, Chinese Journal of Catalysis. 34 (2013) 1402-1406.

- [21] I. Agirrezabal-Telleria, J. Requies, M.B. Güemez, P.L. Arias, Dehydration of d-xylose to furfural using selective and hydrothermally stable arenesulfonic SBA-15 catalysts, *Applied Catalysis B: Environmental*. 145 (2014) 34-42.
- [22] P. Bhaumik, T. Kane, P.L. Dhepe, Silica and zirconia supported tungsten, molybdenum and gallium oxide catalysts for the synthesis of furfural, *Catal. Sci. Technol.* 4 (2014) 2904-2907.
- [23] A.S. Dias, M. Pillinger, A.A. Valente, Dehydration of xylose into furfural over micro-mesoporous sulfonic acid catalysts, *Journal of Catalysis*. 229 (2005) 414-423.
- [24] H. Li, A. Deng, J. Ren, C. Liu, W. Wang, F. Peng, et al., A modified biphasic system for the dehydration of d-xylose into furfural using SO₄²⁻/TiO₂-ZrO₂/La³⁺ as a solid catalyst, *Catalysis Today*. 234 (2014) 251-256.
- [25] S. Lima, M. Pillinger, A.A. Valente, Dehydration of D-xylose into furfural catalysed by solid acids derived from the layered zeolite Nu-6(1), *Catalysis Communications*. 9 (2008) 2144-2148.
- [26] E. Lam, J.H. Chong, E. Majid, Y. Liu, S. Hrapovic, A.C.W. Leung, et al., Carbocatalytic dehydration of xylose to furfural in water, *Carbon*. 50 (2012) 1033-1043.
- [27] A.S. Dias, M. Pillinger, A.A. Valente, Liquid phase dehydration of d-xylose in the presence of Keggin-type heteropolyacids, *Applied Catalysis A: General*. 285 (2005) 126-131.
- [28] A.S. Dias, M. Pillinger, A.A. Valente, Mesoporous silica-supported 12-tungstophosphoric acid catalysts for the liquid phase dehydration of d-xylose, *Microporous and Mesoporous Materials*. 94 (2006) 214-225.
- [29] A.S. Dias, S. Lima, M. Pillinger, A.A. Valente, Modified versions of sulfated zirconia as catalysts for the conversion of xylose to furfural, *Catalysis Letters*. 114 (2007) 151-160.
- [30] E. Sairanen, K. Vilonen, R. Karinen, J. Lehtonen, Functionalized Activated Carbon Catalysts in Xylose Dehydration, *Topics in Catalysis*. 56 (2013) 512-521.
- [31] E. Lam, E. Majid, A.C.W. Leung, J.H. Chong, K.A. Mahmoud, J.H.T. Luong, Synthesis of Furfural from Xylose by Heterogeneous and Reusable Nafion Catalysts, *ChemSusChem*. 4 (2011) 535-541.
- [32] I. Agirrezabal-Telleria, A. Larreategui, J. Requies, M.B. Güemez, P.L. Arias, Furfural production from xylose using sulfonic ion-exchange resins (Amberlyst) and simultaneous stripping with nitrogen, *Bioresour. Technol.* 102 (2011) 7478-7485.
- [33] A.S. Dias, S. Lima, M. Pillinger, A.A. Valente, Acidic cesium salts of 12-tungstophosphoric acid as catalysts for the dehydration of xylose into furfural, *Carbohydrate Research*. 341 (2006) 2946-2953.
- [34] J. Zhang, J. Li, L. Lin, Dehydration of Sugar Mixture to HMF and Furfural over SO₄²⁻/ZrO₂-TiO₂ Catalyst, *BioResources*. 9 (2014) 4194.
- [35] S. Verma, R.B.N. Baig, M.N. Nadagouda, C. Len, R.S. Varma, Sustainable pathway to furanics from biomass via heterogeneous organo-catalysis, *Green Chem.* 19 (2017) 164-168.
- [36] V. Choudhary, S.I. Sandler, D.G. Vlachos, Conversion of Xylose to Furfural Using Lewis and Brønsted Acid Catalysts in Aqueous Media, *ACS Catal.* 2 (2012) 2022-2028.

- [37] O. Ershova, J. Kanervo, S. Hellsten, H. Sixta, The role of xylulose as an intermediate in xylose conversion to furfural: insights via experiments and kinetic modelling, *RSC Adv.* 5 (2015) 66727-66737.
- [38] B. Saez, A. Santana, E. Ramírez, J. Maçaira, C. Ledesma, J. Llorca, et al., Vegetable Oil Transesterification in Supercritical Conditions Using Co-solvent Carbon Dioxide over Solid Catalysts: A Screening Study, *Energy Fuels.* 28 (2014) 6006-6011.
- [39] N. Katada, J. Endo, K. Notsu, N. Yasunobu, N. Naito, M. Niwa, Superacidity and Catalytic Activity of Sulfated Zirconia, *J Phys Chem B.* 104 (2000) 10321-10328.
- [40] C. Ledesma, J. Llorca, Hydrogen production by steam reforming of dimethyl ether over Cu–Zn/CeO₂–ZrO₂ catalytic monoliths, *Chem. Eng. J.* 154 (2009) 281-286.
- [41] O. Ershova, K. Nieminen, H. Sixta, The Role of Various Chlorides on Xylose Conversion to Furfural: Experiments and Kinetic Modeling, *ChemCatChem.* 9 (2017) 3031-3040.
- [42] M.A. Mellmer, C. Sener, J.M.R. Gallo, J.S. Luterbacher, D.M. Alonso, J.A. Dumesic, Solvent Effects in Acid-Catalyzed Biomass Conversion Reactions, *Angewandte Chemie International Edition.* 53 (2014) 11872-11875.
- [43] B. Danon, G. Marcotullio, W. de Jong, Mechanistic and kinetic aspects of pentose dehydration towards furfural in aqueous media employing homogeneous catalysis, *Green Chem.* 16 (2014) 39-54.
- [44] K. Lamminpää, J. Ahola, J. Tanskanen, Acid-catalysed xylose dehydration into furfural in the presence of kraft lignin, *Bioresour. Technol.* 177 (2015) 94-101.
- [45] N. Akiya, P.E. Savage, Roles of Water for Chemical Reactions in High-Temperature Water, *Chem. Rev.* 102 (2002) 2725-2750.
- [46] Z. Chen, W. Zhang, J. Xu, P. Li, Kinetics of xylose dehydration into furfural in acetic acid, *Chin. J. Chem. Eng.* 23 (2015) 659-666.
- [47] B. Danon, W. Hongsi, L. van der Aa, W. de Jong, Kinetic study on homogeneously catalyzed xylose dehydration to furfural in the presence of arabinose and glucose, *Biomass Bioenergy.* 66 (2014) 364-370.
- [48] I. van Zandvoort, Y. Wang, C.B. Rasrendra, E.R.H. van Eck, P.C.A. Bruijninx, H.J. Heeres, et al., Formation, Molecular Structure, and Morphology of Humins in Biomass Conversion: Influence of Feedstock and Processing Conditions, *ChemSusChem.* 6 (2013) 1745-1758.
- [49] C. Sievers, I. Musin, T. Marzalletti, M. Valenzuela-Olarte, P. Agrawal, C. Jones, Acid-Catalyzed Conversion of Sugars and Furfurals in an Ionic-Liquid Phase, *ChemSusChem.* 2 (2009) 665-671.
- [50] K.J. Zeitsch, o. Furfural as a solvent, *Sugar Series.* 13 (2000) 317-318.
- [51] Y. Yang, C. Hu, M.M. Abu-Omar, Synthesis of Furfural from Xylose, Xylan, and Biomass Using AlCl₃·6H₂O in Biphasic Media via Xylose Isomerization to Xylulose, *ChemSusChem.* 5 (2012) 405-410.
- [52] J.B. Binder, J.J. Blank, A.V. Cefali, R.T. Raines, Synthesis of Furfural from Xylose and Xylan, *ChemSusChem.* 3 (2010) 1268-1272.

- [53] J. Iglesias, J.A. Melero, G. Morales, M. Paniagua, B. Hernández, Dehydration of Xylose to Furfural in Alcohol Media in the Presence of Solid Acid Catalysts, *ChemCatChem*. 8 (2016) 2089-2099.
- [54] M. Paniagua, S. Saravanamurugan, M. Melian-Rodriguez, J.A. Melero, A. Riisager, Xylose Isomerization with Zeolites in a Two-Step Alcohol–Water Process, *ChemSusChem*. 8 (2015) 1088-1094.
- [55] M.G. Mazzotta, D. Gupta, B. Saha, A.K. Patra, A. Bhaumik, M.M. Abu-Omar, Efficient Solid Acid Catalyst Containing Lewis and Brønsted Acid Sites for the Production of Furfurals, *ChemSusChem*. 7 (2014) 2342-2350.
- [56] G.D. Yadav, J.J. Nair, Sulfated zirconia and its modified versions as promising catalysts for industrial processes, *Microporous and Mesoporous Materials*. 33 (1999) 1-48.
- [57] B.T. Loveless, A. Gyanani, D.S. Muggli, Discrepancy between TPD- and FTIR-based measurements of Brønsted and Lewis acidity for sulfated zirconia, *Applied Catalysis B: Environmental*. 84 (2008) 591-597.
- [58] G.G. Volkova, S.I. Reshetnikov, L.N. Shkuratova, A.A. Budneva, E.A. Paukshtis, n-Hexane skeletal isomerization over sulfated zirconia catalysts with different Lewis acidity, *Chemical Engineering Journal*. 134 (2007) 106-110.
- [59] L. Filiciotto, A.M. Balu, J.C. Van der Waal, R. Luque, Catalytic insights into the production of biomass-derived side products methyl levulinate, furfural and humins, *Catalysis Today*. In Press (2017).
- [60] V. Choudhary, A.B. Pinar, S.I. Sandler, D.G. Vlachos, R.F. Lobo, Xylose Isomerization to Xylulose and its Dehydration to Furfural in Aqueous Media, *ACS Catal*. 1 (2011) 1724-1728.
- [61] S.J. You, Y.T. Kim, E.D. Park, Liquid-phase dehydration of d-xylose over silica-alumina catalysts with different alumina contents, *Reaction Kinetics, Mechanisms and Catalysis*. 111 (2014) 521-534.
- [62] S. Lima, M.M. Antunes, A. Fernandes, M. Pillinger, M.F. Ribeiro, A.A. Valente, Catalytic cyclodehydration of xylose to furfural in the presence of zeolite H-Beta and a micro/mesoporous Beta/TUD-1 composite material, *Applied Catalysis A: General*. 388 (2010) 141-148.
- [63] S.B. Kim, M.R. Lee, E.D. Park, S.M. Lee, H. Lee, K.H. Park, et al., Kinetic study of the dehydration of d-xylose in high temperature water, *Reaction Kinetics, Mechanisms and Catalysis*. 103 (2011) 267-277.
- [64] P.J. Oefner, A.H. Lanziner, G. Bonn, O. Bobleter, Quantitative studies on furfural and organic acid formation during hydrothermal, acidic and alkaline degradation of D-xylose, *Monatshefte für Chemie / Chemical Monthly*. 123 (1992) 547-556.
- [65] Q. Jing, X. Lü, Kinetics of Non-catalyzed Decomposition of D-xylose in High Temperature Liquid Water, *Chinese Journal of Chemical Engineering*. 15 (2007) 666-669.
- [66] K. Lamminpää, J. Ahola, J. Tanskanen, Kinetics of Xylose Dehydration into Furfural in Formic Acid, *Ind Eng Chem Res*. 51 (2012) 6297-6303.
- [67] T.M. Aida, N. Shiraishi, M. Kubo, M. Watanabe, R.L. Smith Jr., Reaction kinetics of d-xylose in sub- and supercritical water, *The Journal of Supercritical Fluids*. 55 (2010) 208-216.
- [68] M. Al-Hazmi, A.W. Apblett, Benzylolation of benzene over sulfated zirconia supported in MCM-41 using a single source precursor, *Catal. Sci. Technol*. 1 (2011) 621-630.

- [69] T. Eifert, M.A. Liauw, Process analytical technology (PAT) applied to biomass valorisation: a kinetic study on the multiphase dehydration of xylose to furfural, *React. Chem. Eng.* 1 (2016) 521-532.
- [70] A. Casanovas, C. de Leitenburg, A. Trovarelli, J. Llorca, Catalytic monoliths for ethanol steam reforming, *Catalysis Today*. 138 (2008) 187-192.
- [71] R. Karinen, K. Vilonen, M. Niemelä, Biorefining: Heterogeneously Catalyzed Reactions of Carbohydrates for the Production of Furfural and Hydroxymethylfurfural, *ChemSusChem*. 4 (2011) 1002-1016.
- [72] Y. Wang, K. Lee, S. Choi, J. Liu, L. Wang, C.H.F. Peden, Grafting sulfated zirconia on mesoporous silica, *Green Chem.* 9 (2007) 540-544.
- [73] H. Yang, R. Lu, J. Zhao, X. Yang, L. Shen, Z. Wang, Sulfated binary oxide solid superacids, *Mater. Chem. Phys.* 80 (2003) 68-72.
- [74] M. Haneda, K. Takamura, Y. Doi, N. Bion, L. Vivier, Synthesis of ordered porous zirconia containing sulfate ions and evaluation of its surface acidic properties, *J. Mater. Sci.* 52 (2017) 5835-5845.
- [75] S.L. Goertzen, K.D. Thériault, A.M. Oickle, A.C. Tarasuk, H.A. Andreas, Standardization of the Boehm titration. Part I. CO₂ expulsion and endpoint determination, *Carbon*. 48 (2010) 1252-1261.